

**THE
ART AND MYSTERY
OF A
CORDWAINER;
OR,
AN ESSAY
ON THE PRINCIPLES AND PRACTICE
OF
BOOT AND SHOE-MAKING.**

WITH ILLUSTRATIVE COPPER PLATES,

By JOHN F. REES

LONDON:

PRINTED FOR GALE, CURTIS, AND FENNER,

PATERNOSTER-ROW

1813

Printed by Richard Taylor and Co., Shoe-Lane

PART I (Assembly)

Thread and Wax

The first thing done in the trade, is the making a thread; and a thread well made contributes as much as any thing to a good solid boot or shoe. And as a thread is composed of many strands of hemp or flax, and wax, I shall treat on each separately. — First of,

Wax

Wax should be made of the best black pitch, and a fourth part of rosin, and a little fine oil if you should find it hard, which you will in winter; but put no fat nor grease, for neither will incorporate with the pitch so well as the oil: for wax that is made with fat or grease, will not properly adhere to the thread or work. The pitch should be melted in an earthen or an iron pot, on a slow fire, that it may not burn. When thoroughly melted, take it off the fire and pour into it as much oil as the season requires, and let the whole be well stirred; then pour it into a pan or tub of cold water, and press it close together in the water, that it may be as free as possible from air bladders, and let it be taken out of the water while warm; and then draw it between the hands to that the degree that it may support itself in small filaments or threads without breaking. Unless it be brought to that ductile state, it will be too brittle to be of any service, it will fly off the thread in the working, and that which remains will soon wear off. Therefore, unless the wax be of that ductile property, capable of adhering to the thread, the work cannot be firm.—
Secondly of,

Threads.

Sewing threads should be made of the best long green hemp that can be had; and stitching threads of the best yellow or gray flax, and not too hard spun, for the faculty of making the threads and of better receiving the wax.

When you have got these materials, cast out from the ball of hemp or wax the first strand to the length the work requires; but never longer than what you can draw out on two pulls with ease; for longer will cause you to lose time, as well as render the thread unfit for use, from the too great friction such lengths must acquire in the work.

All of the other strands must be gradually shorter than the first, that the ends of the threads may be tapering, but yet strong. A little experience will teach the young practitioner this, as well as putting on the hair or bristle, which is the next article. But before that is done, let the thread be well waxed before you twist it; for previous to the twisting the wax enters the body of the thread, and then every strand is covered with it. Let the thread be well twisted, but not too hard, and rub it smooth with a bit of upper leather; and let it be waxed over again before you put on the bristles.

In putting on the

Bristles,

Some split the bristle from the soft end to a certain distance, then putting the point of the thread in between the slit, at the lower part of it, and holding the bristle in the left hand between the fore finger and the thumb, with the fore finger and thumb of the right hand twist up hard the split part of the bristle; and then with the fore finger and thumb of the left hand twist up hard the point of the thread and bristle together, and so alternately till it is nearly twisted to the split end of the bristle; then put on the end a knot, or make a hole with a small awl in the thread, and put the hard end of the bristle through; others will twist the point of the thread round the bristle without splitting it and fasten it the same as above.

The points of the bristles should be cut off and pointed, by giving them a few strokes backward and forward on a whetstone; for without pointing them, you will not be able to get them through stuff work; and in all other kind of work you will find it to your advantage.

Before I close this subject, I would have you to be very particular in choosing the best green hemp for to make your sewing threads, where the work is require very strong, whether it be in town or country.

Closing

Of upper leather for shoes: it consists of two parts, viz, round and flat seams.

All grain leather is closed on the flesh side with a round seam, and wax leather is sometimes closed inside with a round seam. But, some years back, all wax calf leather was closed on the wax side with a flat seam, and all hide leather, whether grain or wax, was closed with a round seam; but now the general mode of closing wax calf leather is on the wax side with a round close, and set as if closed flat. Certainly a round seam is the firmest, if care is taken in the setting of it, that the stitches are not injured by the iron setter.

Round seam.—As the two quarters of the shoe are first closed together, let the upper part of them be placed even on the closing block under the stirrup, with the edges close to each other. Now, with a proper awl* and thread,

*The awl should be well polished, and round except at the very point, there it should be rather flat, that it may enter the leather with more ease; let the awl at all times be quite as full as the thread that you are using. For when the two threads enter the hole, and if the hole be too small, it will strain the threads, and free the wax from off them, and the wax will be left on each side of the hole, and the threads will be deprived of that wax, which should have entered with them into the work to render it firm.

Nor should the awl be so full as the two threads, for in that case the thread and wax will not be full enough to fill the hole of the awl with that extension or bulk for to enter firm into the work.

rise a hold on each side in proportion to the substance of the leather, but never let it be too full, if it be grain leather, let the awl come out near the grain at the edge on one side, and enter the other edge at the same distance from the grain; but if it be wax leather, let it be split a little more than one half towards the grain, but not so near the grain as that of grain leather, otherwise the outside seam will be too open.

By spitting the leather, the two rough ends will come in contact with the intervening wax that issues from the threads, and will form a solid firm seam. Let the threads form half knots, commonly called half cast, for, by that, there will be more thread and wax in the work, and you can draw the stitches as tight as you please without causing the leather to grin or tear: and in all kind of sewing, you should observe the same method, except that of sewing down the heel of a man's shoe or a channel.

The practice of closing the two black sides together cannot be so firm as that of splitting; for the two greasy sides of the leather coming in contact with the intervening wax, cannot adhere, from the natural properties of each: therefore, from the above reasons, splitting is the best method. I do not mean, from the above, that the wax is to issue out from between the seam in that quantity as to be always perceptible;—no;—but that you are to understand that when the threads are felt to come through the work full, there issues from the threads imperceptibly a certain quantity of wax, which enters into the ports of the leather and between the seam, as a defence to the threads in the work from wet and damp. Hence, the threads should be waxed at certain intervals to supply the constant drain, and to keep them nearly in the same state as when they were made. The necessity of paying strict attention to this article, causes me the more to impress it on the young mind as a very important part of the work.

Again to the subject: continue the same hold through the whole heel steam; and if there be any difference in the depth of the quarters, let it remain at the bottom, When you have done with the heel seam, the same threads will serve to close the side seams, if they be of the usual length at first, about a fathom and a half. If the side seam be square, (though there are but very few of them now,) you must be careful to let the corner of the side of the vamp come up full to the angle of the side of the quarter, and begin at the bottom where they meet; and when you have closed up to the angle of the quarter, let a hold be taken in the length of the quarter right over the angle, and the thread on the quarter side be put through, and brought parallel

with the length of the upper part of the side seam, that the corner of the seam may be square on the quarter side.

In closing the upper part of the side seam, let the quarter side be strained a little more than the vamp; and when you come to the opening of the vamp, be careful to let the end of the quarter lie straight on the vamp; but if inclined, let it incline down towards the edge of the vamp, that the upper part of the quarter may be strained, as it will last the easier, and fit the closer round the ankle when on the foot. But if it should incline upwards, it will have the contrary effects, bad lasting and bad fitting.

If there be a slit in the vamp to let the end of the quarter in, keep the quarter a little strained, and if the slit be not long enough, which is sometimes the case, you are to cut it so.

At the end of the quarter, stab a hole through the vamp, close to the last stitch on the vamp side, and let in the thread which is on the same side; then at the end of the quarter, about the distance of the breadth of the seam from the seam on the quarter side, let there be a row of stabbing to the opening of the vamp, and there let both threads be brought inside, and fasten them with a knot or a few stitches up the opening.

The other side seam to be done the same.

It is immaterial which of the side seams you begin with.

Flat closing

Is looked upon as neater than round.

If the leather be stout, you must pare off about one third of its substance at the edge, from the flesh side; but the inclination to the flesh side to be very little, nearly to a perpendicular. The directions with respect to the awl, thread, and quarter, to be the same as in the last article. Let the hold be in proportion to the substance of the leather, but never very wide. Let the point of the awl come out at the lower part of the paring slope, and enter the

other side at the same place, and so continue through the whole closing.

In the last article I mentioned only of square side seams; but the general mode of cutting shoes now, is to have but one straight seam to the opening of the vamp, and the end of the quarter to have two rows of stabbing. Be careful, before you begin to stab the end of the quarter, to let it incline rather downward towards the edge of the vamp.

If the leather be thin, it will not bear paring; therefore, in taking the hold, the point of the awl must come out at the edge close to the black, and enter the other side the same, and so on through the whole closing. These are the only kinds of closing used for shoes.

With respect to

Boot Closing,

It partakes of both: for, in closing the tongues of cordovan boots, the hold in the leg is flat close, and the point of the awl comes out even with the grain or black side; but the hold in the tongue of the vamp is of the round close, and the awl enters in close to the black edge. Calf legs likewise partake of both kinds: the hold in the tongue of the vamp and back strap is round close; but in the leg it is flat close. The beauty of all kinds of closing is, that the hold is equal on each aide, and the stitches of the same length and regular.

When setting the seams, you must be particular that the iron setter is not above blood heat, otherwise it will burn the seams. In setting the seams you should use a little gum water and colouring, which will make the seams smooth and hard: for without, the warm iron will not slide so well on the seams. But above all; be careful that there is no kind of cutting edge to the iron, but that it be perfectly smooth.

This article refers to the setting of the seams of shoes as well as to those of boots.

Lining

The back piece should be as deep as the quarter at the heel seam, and cut square at top, about an inch and a half wide, and then cut it on both sides from the top downward with a short curve at first, and then with

a gradual slope to the ends, letting them be about three quarters of an inch deep: then let the side linings be cut even at the ends, to meet the back piece, and of the same depth with it at the ends. Then lay the vamp and quarter flat on a board, and lay the lining on them from where the end of the back piece joins; then mark it in a gradual inclining slope from the end to the opening of the vamp; and if the vamp have no lap lining, there the lining must be notched, and a sloping bit let up the opening about half an inch long, and from the opening of the vamp let the lining be cut in a gradual slope to the toe, and at the toe to be about half an inch wide. The others are to be cut to this, and to be pared at the edges that are to be sewed if the leather, be thick. The sewing of the lining of strong shoes is done with a wax thread and an awl. The thread should be made of three cords of flax, and the awl should be rather flat and crooked at the point. The side lining should not be sewed above two or three stitches on the vamp, beyond the quarter, for it will be the means of breaking the vamp at the joints. Let the awl enter the lining first, as it can bear the fullest part of the awl better than the upper.

In shoes that are made in cities and large towns the lining is sewed with silk, and is the province of the needle; but the same order in the sewing should be observed as in that of the awl.

Man's Shoe.

The bottom stuff (as the sole leather, &c. is commonly called) should be previously wetted in a tub or pan of clean water, but not too wet, and left to remain together in a heap for about half an hour, that the water may enter the pores of the leather, to render it mellow and pliable for the work.

If the soles and inner soles be each in a piece, mark them to the last, and cut them separate: with the top-pieces do the same. Then pare off the loose flesh from off the stuff, and let the seat lifts be split as slanting as you can. Then with two pair of pincers stretch the stuff well across a block, and particularly in the width, and let it be well hammered*. Then mould the soles to the last and put the heel stuff in such a place, that it may get dry by the time you think that you shall use it.

*Some do not hammer the soles till they are going to use them, that they may work the easier, and feel the harder when the shoes are finished, as they think.

But experience tells us that leather will shrink much in drying, and if a shoe be soon finished, the sole will part from the welt, and grin, let the shoe be ever so well put together in every other respect.—But it is not the case when hammered and put to dry; and when you are going to use, them, to damp them, and slightly hammer them over again.

Now that you have the stuff and uppers prepared, fix the inner sole on the last, and fasten it with a tack to the last about the middle of the waist, and rest the last on your two knees, with the sole upward, and support it there with the stirrup: then strain the inner sole forward towards the toe, and fasten it to the last about two inches from the toe, and do the same to the heel part. Then strain it moderately all round the last, and secure it to the sides with some tacks. Hammer the inner sole moderately to the last, that it may keep its position. Be careful that the inner sole be not too wet, only that it may be mellow and pliable; otherwise the thread and wax will not have that effect they ought to have, and the sewing in all probability will rip.

Nor should you overstrain the inner sole on the last; for all leather when overstrained, whether wet, or dry, but more so when wet, because it gives more then, will contract or shrink to its former position gradually as it dries when the straining force is removed; therefore the inner sole will become narrower than you intended it should be. Some may say that the inner sole will keep its position after the shoe is sewed, but reason and experience inform us to the contrary: indeed, only the interval of time between the rounding of the inner sole and sewing of the same, produces a full proof if the inner sole be too wet.

After you have taken the straining tacks out of the last, round the inner sole just to the edge of the last, unless you have orders to work fuller or narrower than the last. Mark on the inner sole the length of the

heel, which is in general from two inches and a half to three inches; but there is no certain rule, for it depends on circumstances and the nature of the work. If the customer that the shoes are for has a long flat seat to his foot, the heel of the shoe must be long, otherwise the shoe will be uneasy to him; and in the wear of the shoe, he will force down the soles nearly even with the top piece at the end of the heel.

With a shoulder stick of a certain breadth mark off on the edge of the inner sole for a feather round the fore part, from the mark of the heel on one side to that on the other. The breadth of the feather must always be in proportion to the substance of the work, it must be full as wide as the thickness of the upper leather, lining, welt, and the distance of the stitching stitch from the upper; therefore the stouter these are, the wider must be the feather.

There are some that do not put a feather to a boot or shoe; but boots or shoes so made can not wear well, for the upper leather will break all round the fore part close to the sole. Because in this case the upper leather will ply short against the hard edge of the inner sole, which will cause the upper leather to break. But in the case of a sloping feather, that lies on the inside of the upper, full as far as the stitching stitch, it will cause the upper leather to ply in a curve or sweep, which will always prevent the upper from breaking off short.

For example: if you take a twig or wire, and bead either of them backwards and forwards in a curve or sweep, it will not break very easily; but if you will ply either of them short, it will break instantly.

Therefore all boots and shoes that are intended for service should not be made without such a feather; especially at these times, when leather is so badly tanned and curried.

The feather must be of a gradual slope from the mark to the edge; but only at the edge it is to be thin.

Likewise let there be a feather to the heel part as wide as the substance of the upper lining, and what will cover the rand when made*.

* Though some will give feather to the fore part, they will give none to the heel part; but for the same reason as above, I advise every one to do it to every kind of work that is for service.—Very light or dress shoes, where the work is required very close, are out of my present question.

The next thing to be done, is to hole the inner sole; but as a guide for the young beginner, and if the insole be thick, take a shoulder stick and mark off from the mark that was made for the feather, further on the inner sole, a width equal to the length of the bold, which should be equal to the thickness of the upper leather, lining, and welt; then: with the point of the knife cut a shallow channel* perpendicular to the inner sole; in that mark and pare off from that; channel sloping to the middle of the inner sole a thin skiving all round the fore part; this will cause a ridge between the channel and the feather of the inner sole, equal in width to the length of the hold.

*But if the inner sole be thin, hole it without.

This hold on the inner sole, being equal to the thickness of the upper leather, lining, and welt, will be sufficient to take up on each side an equal quantity of thread and wax: therefore a wider bold on the inner sole side would render the work too extensive for the threads to have their proper effect, because they could not be drawn in close enough. On the contrary, if the hold be too narrow, it is liable to break out, and will not take in a sufficient quantity of thread and wax to support the work.

Now with an awl rather crooked hole the inner sole, and let there be four or five stitches in an inch at least round the fore part; but in the heel part, if what is called a blind rand, let there be but three.—The number of stitches depends much on the quality of the work; that is, whether it be light or heavy. But mind this, if the stitch be too long, the work cannot be firm, and if too short, it is liable to break through.


The next thing you have to do is

Lasting,

And let the heel-seam of the quarters be fixed exactly even on the middle of the heel part of the last, and fastened there, by putting a tack through one of the quarters close to the seam, about an inch from the upper part of the quarter, and another at the bottom, near the edge. Always mind to sink no more of the quarters below the last, than what is necessary under the sewing stitch, except when the upper leather is much too wide in the instab, that you are obliged to sew off a large portion of the fore part of the quarters; then it will be proper to sink the hind part to bring it even; otherwise the quarters will bulge out at the sides, and never fit well.

Let the fittings or instab leathers (if it be not a block last) be fastened to the last with a small tack near the toe; then let the upper leather be drawn gently over the toe of the last, and the crease or middle of the vamp come directly over the middle part of the toe of the last, and with the pincers strain it moderately over the toe, and secure it on the sole side with a tack.

Then at a certain distance from the toe, with the pincers, strain the upper leather tight in the direction of the line AB as in fig. 1st; that is, from the upper end of the quarter at the heel seam, in a direct line along the end of the side seam to the side of the toe; and the same on the other side.

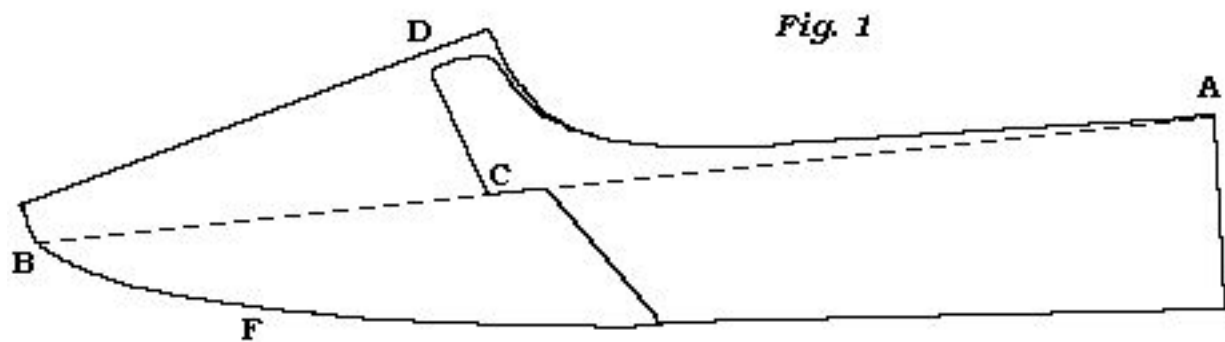

Be careful that they are even on each side, for they are the two principal lasting tacks. If they are not carefully lasted, the upper leather never will be smooth; therefore too great care cannot be taken of them, that they may be equally strained at the same distance from the toe in the above direction*.

*I have known very good old hands in the trade in every respect but that of lasting; and in that they seemed to be like young beginners.

The next two tacks are those at the joints, as at C.: they last the upper tight over the instab and joints. Let the upper leather be lasted direct downward; but if it should incline, let it incline forward.

Let the ends of the side seams be always at the same distance from the toe, and the same depth from the edge of the last. Never last the quarter beyond the end of the side seam, towards the heel seam, except the quarter be too shallow to come under the sewing stitch: and in that case, it is better to take an instab leather out of the fittings, and endeavour to shove it in after the shoe is sewed.—But if you do take a leather out, you must last the upper over again, otherwise the upper leather will not be smooth.

The next two tacks are those between the joints and the lasting tacks, as in fig. 1.. between B and C.—The next thing is to last the toe; that is, you must take out the toe and the two lasting tanks, and turn up the upper over the toe, and take out the tack from the instab leathers, or fittings.—Then draw the side linings close together, and let a tack be put in each, and let the ends be cut to meet, and with a small end brace

them together.—Then cut the Lining on each side from the joint sloping towards the toe: skive the edges, and put a little paste slightly over them; then draw the upper leather over the toe, and see that the lining keeps its place.

After you have secured the upper leather over the toe, let the two lasting tacks be properly strained in the direction as given above.

Then last the toe, by putting a tack or two between the lasting tacks and the toe tack, on each side, as in fig. 1. between B and the toe.

Then brace the toe, by taking the end of a wax thread, and with an awl let it enter the inner sole below the lasting tack, and let it come out in the upper close to the tack that is between C and B, and let it come round the toe, and its purchase on the tack that is on the opposite. But take out the tacks from one lasting tack to the other round the toe, that is, from B to B round the toe, before you fasten the thread; and strain the upper leather back against the thread, till you bring the thread and upper to lie just on the outer holes of the inner sole; and let the upper leather be smooth and free from plaits or wrinkles round the toe.

Though some do not brace the toe, but take the tacks out as they sew; but I advise the former mode.

Now after you have lasted the upper, put a little paste on it, and with a damp sponge let the paste be well rubbed over the upper, to keep the grain smooth in the work, if it be wax leather.

In the next place prepare the welt, by skiving it to the substance the work requires, and let one side be thinned to receive the thread, but in, proportion to the work and thread: for to a strong and serviceable shoe the welt should not be reduced too thin.

The next article is a sewing thread: and the sewing thread should be made of the best green hemp, and well waxed, (as I have directed in the early part of this work,) and its size full in proportion to the work; for it is better for the thread to be, of the two, too full than too small, (unless it be a dress shoe, for that is more for sight than wear,) for if there be hardly any thread, there can't be much wax; and if there be not sufficient thread and wax in proportion to the work, the shoe can never be firm.

In Sewing,

Begin with the back part of the shoe, for the rand of the heel requires the best part of the thread; and let there be a full cast to every stitch on the quarter side, and let not the stitch be drawn too tight on the quarter, that the stitch may lie close and smooth, in sewing down the heel, without causing the quarter to grin or tear. And if you should neglect either or both of them, you will find great difficulty to make the rand; besides being liable to tear the quarters.

When you have sewed round the heel, the first stitch in the fore part must come over the end of the welt, and with the thin end of the hammer let the welt be laid close to the upper that lies even with the outer [h]oles of the inner sole, and so you must continue to do for about every eight or ten stitches while you are sewing the fore part.

Likewise you must be careful to wax the thread so often as that it may be kept nearly in the same state as it was when you began with it.

In drawing the threads in sewing, you will find that on one side the end of the thread in hand will come out at the hole nearer to you than that part that goes in at the same side; and on the other side, the end in hand must come out at the hole further from you than that part which goes in on that side: therefore the stitch on the latter side will have the appearance of a half cast, which should always be on the welt side, as it will prevent the welt from grinning.

The sewing awl should be curvilinear, or have a bend similar to that which is called pump blade, because, in consequence of the curve or bend, you can rise the hold in the upper leather and welt in the exact point you wish to; but with a straight awl it will be out of your power, for the straight awl will rise the hold far beyond

the proper place: therefore the parts will never be brought close enough together.

After you have done sewing the welt, lay with the hammer the stitch smooth, and pare off the spare leather of the upper and lining close to the welt; and if that part of the welt above the stitch should not be even, pare it so, but not too near the stitch.

The heel part must not be pared, but laid flat with the hammer; and rise the stitch with some straight awl; and with a shoulder stick set the stitch smooth on the welt side of the fore part.

Then lay the best split-lift on the heel part with some tacks, and let it be about a quarter of an inch beyond the outside of the stitch and let the ends come quite flush with the ends of the welt. With the edge of the hammer settle the split-lift, and instead of the tacks put in some pegs; then pare and rasp it even.—Fill the middle of the fore part between the sewing, with skivings of leather, and some paste, for to level the middle with the prominent part of the sewing seam; otherwise the sole will not be even, but in pits and ridges, which will not work nor wear well.

Now let the sole be wetted, so as to be pliant and mellow, and hammer it over slightly, and lay it on the insole, after every thing is done as above directed, and a little paste put between.

Secure the sole in the waist with a tack about two inches below the joints; then draw it over the toe, and secure it with a tack about two inches from the toe, and with two tacks fasten it at the heel part.—Then settle the sole well, and pare it round the fore part at a certain distance from the sewing stitch on the welt side: which distance depends on the substance of the shoe, and it must correspond with the width of the feather of the inner sole; for, if the sole be left wider than the feather of the inner sole, the fore part will project or shelve out frightfully beyond the upper leather; and if too much under the feather, it will cover the welt and bury the work, and the welt will be too close. But in rounding the sole to the welt, you must be careful to leave enough of the sole to pare off in making the fore part after stitching; therefore there must be enough left to clear the sewing stitch, to receive the stitching stitch, and to make the fore part.

Now you have rounded the sole, take the thin end of the long stick, or thin bone, and force down the welt to the sole from the upper, all round the fore part, as smooth as you can; then, with a thin bone, or iron, work out the welt from the upper towards the edge as much as you can, that no loose welt may remain between the stitching stitch and the upper leather.—Then pare off the spare welt that is beyond the sole, and with the end of a thin bone, or iron, press the welt to the sole all round the fore part, at that distance from the upper leather as to clear the sewing stitch, that it may make a groove kind of impression on the welt where you intend to stitch.

Before you begin to stitch, put on the piece sole, as it will prevent the split-lift to move from its place; but in putting it on, let there be little paste put between, and let it lap over the edge of the sole, for it is much better than to let them meet plumb. In the latter case it is liable to shrink and leave a vacancy between, to the injury of the shoe, and unsightliness of the work.

The stitching thread must be in bigness proportionable to the work; but it is better to be full than too small, for the work will look better and wear firmer than when too small.—Let it be but slightly twisted, that the stitch may lie flat on the welt, though the work is always better for the thread being well twisted, if it has been well waxed before; but if there are a great number of stitches put in the welt, this makes up for the want of hard twisting—Make two threads of about a fathom and a half long, which will answer for a middle-sized shoe.

Always make use of a square, or what is commonly called French awl blade, flatter in the depth than in the width.

Let the first hole be made through the split-lift and sole at the end of the welt, that the first stitch may come over the welt.—In stitching, mind that the thread in hand on the welt side is nearer to you than that which goes on the welt, that you may always have the stitch fair and regular.

The number of stitches to an inch on the welt depends on the substance of the shoe: in a middling shoe, about twelve stitches to an inch will be sufficient ~ and more or less as the shoe is light or heavy: too many will tear the work, and the contrary will not hold it together.—Wax the threads as often as you see they require, that they may be kept nearly in the same state as they were when you began with them.—Cut

the channel in the sole inwards, by beginning on the tight side, when the sole is up, and the toe towards you, and as near the edge as the groove on the welt is from the edge*.

*In stitching, mind to clear the sewing stitch, that the awl does not enter into tiny part of the sewing.

After you have stitched, close up the channel, and with the hammer lay the sole smooth, and scour it out, and slick it well with the long stick; then with a piece of sole leather, thinned to the edge, run it behind the stitch and the upper, which will lay the stitch smooth.—Then take the thin bone, or iron, and run it along the welt on the outside of the stitch, to rise the stitch up smooth and regular. Then with the point of the knife take off the welt from the stitch at a certain distance from the stitch; that is, for a stout shoe at the distance of full the height of the stitch; of a middling, not quite so high as the stitch; and for a light shoe, nearly close to the stitch*.

*How ridiculous it is to see a strong labouring man's shoe with a welt light enough for a dress shoe! and in such case, the stitches will be out in rags at the edge of the welt before the sole is half worn out. The welt in front of the stitch should be full or close as the shoe is stout or light.

Then pare the sole and welt round the fore part plumb or square to the edge of the welt, and with the rasp lay smooth the paring of the knife, and with a bit of glass lay smooth the roughness of the rasp. Then lay a little soft paste over the stitches round the fore part, and with an iron jigger set the welt and stitches. You should have by you three kinds of jiggers, full, middling, and light.—But in setting the welt with gum water, be careful that the iron is not above blood heat; for, if it should, and that it should bear on the upper leather, it will certainly burn the leather, for no upper leather can bear heat above blood heat, without being scorched.

Likewise, be careful that that part of the iron which is between the stitch and the upper leather does not bear on the upper leather; for, if it should, the friction of the iron against the upper leather will cause it to tear as if it had been cut with an edge tool.—Now after you have set the stitches, take the shoulder stick or iron, and set the fore part all round so hard, that the impression may be visible at the edge of the sole, without any future false means; but previously let the edge of the sole and welt be damped with a little thin gum water or paste: and if it should get dry, moisten it with your tongue now and then.

The next part is to make the

Heel.

In the first place, let the heel stuff be perfectly dry and well hammered, so that the lifts, &c. may be hard and dry. Level the sole and piece-sole, and rasp them; put a little paste on the part where the split-lift is to be placed. Fix the split-lift with a few tacks; pare it round the heel close to the sole: then in room of the tacks put in as many pegs, and with the hammer lay it smooth, and level it with the knife, and rasp the grain off and put some paste over the split-lift and sole, and fix on the lift, and proceed in the same manner as you did with the split-lift, &c.

The common height of the heels of men's shoes now, is only a top piece above a split-lift: but whether the lifts be more or less, you must be careful that the heel is quite level before the top piece is put on, that no part of the top piece in substance is pared off. After you have proceeded with the lifts as above directed, fix the top piece on with two or three tacks, and with the hammer settle it smooth,—pare it round to the size and form you intend the heel should be; but be careful that the heel is not made too narrow for the width of the shoe. Cut the channel as near to the edge of the top piece, as you think the point of the heel awl will come out at with ease.

Then hole the heel all round, with the awl resting on every link stitch of the rand, except the first and last, which must be before and after the stitch. In holing, the lifts will be moved out of their place, therefore you must settle them down with the hammer before you begin to sew.

The heel thread must be full, well waxed, and well twisted. In sewing, be careful that in drawing the link stitch close you do not tear the quarters. When the heel is sewed, close the channel, and settle the heel well down, and with the thin end of the long stick, or bone, rub down smooth the stitches of the rand.

Then pare off about: a third of the lower side of the seat lift, and with the corner of the hammer turn up the seat lift over the stitch; pare the upper part of the seat lift as near the stitch as you can, so as to leave enough to cover the stitch; then put a little paste between the seat lift and the stitch, and with the hammer lay the seat lift close to the quarters of the shoe; then put some paste on it, and with the back file, file it hard on the stitch and close to the quarters; but be careful that the back file does not fret the quarters. Pare the seat lift and sole, at the side, as close to the quarters as you intend the width of the rand to be; and that must be wide, middling, or close, as the work is strong, middling, or light; then with the rand bone, or iron, set the rand with a little paste under the setter. Then pare the top piece to the size and form you intend it to be; but that you should always do before the heel is sewed, for now you are confined to the channel.

Now, as you have got the top piece formed, and the rand set, let the heel be pared plumb or square to answer the rand and top piece, and with the rasp take off the roughness of the pareing, and with a piece of glass smooth that of the rasp; then put a little paste over the heel, and with a scouring stone rub it well all round; and when done, wipe the paste clean off the heel, and with a rubber slick it well. If you have in the work flattened the rand, set it again, but not with paste, but with a little gum water.

In the next place, take the tacks out of the top piece; but previous to the paring of the heel, you should have put four or five pegs in front of the heel, and fill the holes with pegs, and with the hammer lay the top piece even,—scour it out with a little paste, after you have rasped and scraped it smooth, and slick the edges-of the top piece smooth.

Then, with a pointed knife cut the front of the top-piece of a curve form, but hardly differing the eighth of an inch from that of a straight line; likewise cut the lifts in a perpendicular line with the front of the top piece; but be careful that the knife does not enter the sole.—Now with the end of the long stick slick the front of the heel, and the adjoining sole, and cut down plumb or square the corners of the heel; but always mind that they do come forward on the sole about an eighth of an inch beyond the welt;—the shoe will not only appear better, but will be firmer.

Now clean the shoe well from all dirt, and slick the bottom well, even if it is to be buffed after; prick the stitches of the fore part, and set them, and likewise the rand. Then colour the heel and fore part, and when dry, rub them hard with a piece of flannel, and slick them well, and with a black ball, ball the heel and fore part well; then with a thumb leather spread it even, and with a warm stone rubber set the ball on the heel, and with a warm iron set the rand and fore part. But observe, the balling part may be left till the shoe is taken off the last, which is generally done by many, when they have light work, to prevent malling the stitch and the ball in taking the shoe off the last. When the shoe is taken off the last, bruise the points of the pegs inside of the heel; and with the crooked knife cut them off, and clean out the seat of the heel, and with the end of the long stick lay down the feather of the inner sole to the welt and rand; then rub down the roughness on the inside of the inner sole, and let the upper leather be smooth and even over the welt and rand; and with a damp sponge and a little soft paste lay the grain of the upper leather smooth, if it be wax leather.

So far, with respect to you, the shoe is done.

Before I quit this article, I advise you, always before you begin the heel, to have all the lifts that are to be in the heel to be quite dry, and hammered the second time; and that every lift be well settled, levelled, rasped, and pasted, before the next is put on: otherwise you will have but a spungy heel, which are too

common in these days, since pegging the heels is out of use; but, by following the above directions, the heel will stand the wear and the shop.

To make a Man's Pump.

Let the stuff be fitted like that of the shoe, only that the soles must be moulded with the grain side to the last.—Here you are to begin with the sole, and not with the inner sole as in the shoe. With a tack, fix the sole to the waist of the last, with the grain of the sole inwards; then with the back of the knife mark the sole across, where the length of the heel is to be, and let the knife enter the sole on each side to the side of the last, which will divide the heel part from the fore part.

Pare the sole round the fore part close to the last, and to the form you intend it is to be, if it be to deviate from the shape of the last; and then with a piece of thin horn between the knife and the last, pare the sole plumb to the last.— Then with a shoulder stick mark off on the sole, a space that will be equal to the thickness of the upper leather and lining, with about an eighth of an inch for paring, and for the upper to lie free and easy at the edge of the sole: and from the mark, skive off to the edge of the sole as much as will reduce it to the substance the edge is required. Likewise, as a regular guide for the awl in taking the hold on the sole, mark off on the sole within the first a space full equal to the substance of the upper leather and lining; and if the sole permit it for substance, cut a very shallow channel, and bole the sole round the fore part between the two marks; but be careful to let the hold on the sole side be very little wider than the substance of the upper leather and lining, for the same reason as given in the direction for the inner sole; which look to. Now, fix the upper-leather on the last with the lining-side outward, and last the upper-leather the same as in the direction given for the shoe; only you must not put in the whole of the fittings as in that of the shoe; but must leave out an instab-leather equal to the difference between the substance of the inner-sole and sole, otherwise the pump will be too wide; therefore a block last is not very convenient for to make a pump on. Let the thread be made in proportion to the work, in bigness, but rather full than otherwise: and in sewing, let there be half cast on the upper-leather side; and let the stitch be drawn-in tight with the hand-leather, unless the pump be very light; for when the thread is round the hand-leather, and the fingers resting on the side of the knee, you have greater power to draw-in the thread with the awl-hand; for, according to the law of mechanics, action and reaction are equal ~ therefore, even in light work it should be made use of, not only the work is firmer, but the seams will be closer, and the work will appear better.

When the pump is sewed, lay the stitches smooth and pare off the spare upper-leather and lining even with the sole, and rub it down smooth.

Then take the last out, and turn the pump, put the last in again and rise up the quarters, let the whole fitting be put in, and with the hammer work out the sole in all directions, and hammer it down even; then scour it out well, and run a thin bone between the edge of the sole and the the upper leather, and with the same bone, or a piece of flat iron, resting flat on the upper leather, close to the edge of the sole, and hammer it, or press the upper leather with it close to the last, and then slick the sole well to the last.

Now, take out the last, and put the inner sole on it and round the seat of the inner sole the same as that of the man's shoe; which see. The fore part must be rounded just as you think that it will cover the sewing stitch of the sole, for wider than that it will press too much against the upper-leather, and will cause it to project or bulge out too much beyond the edge of the sole; but still it must be as wide, so as to cover the seam of the sole. Then skive off a feather from the edge of the inner-sole, of the same breadth with the of the width of the sewing seam of the sole, so that the whole substance of the inner-sole may fill up the vacant space on the sole between the seam on each side. Put a small peg in the inner sole at the toe, and with the point of the knife make a short slit from the peg inward quite through the sole, that the last may slip out with ease when the pump is made.

Now take out the tacks, and paste the fore part of the inner sole, and put the last and inner sole into the fore part of the pump, and be careful that the inner sole is even, and that it covers the sewing seam of the

sole regularly on each side; then secure it there by a tack put through the sole at the waist, and get up the quarters, and let them come up so high as that the lower part may be so much below the holed part of the seat of the inner sole, as what is sewed off them in the fore part: if higher, it will cause the quarters to sit loose at the side, when the last is out.

Now put the whole of the fittings in, and put the straps together, but do not strain them, and put a tack in at the heel seam - to secure the quarters in their place. With the hammer lay the sole smooth and even, and slick it down well to the inner sole. Then make the heel as directed in that of the shoe. When the heel is finished, take the thin bone and run it gently round the fore part to force the sole from the upper leather, and pare the edge of the sole a little sloping towards the sole; but if it be a very light or thin edge, let it incline towards the upper leather. Be careful not to pare the sole under the sewing stitch of the fore part, but let it be a trifle beyond the stitch, for you will make a better edge, and the pump will wear longer.—Then take the paring horn and put it between the knife and the upper leather, and pare off the ragged or fleshy part of the sole.

Now slick the edge of the sole down to the upper leather, on the sole side; and put a little paste on the edge, and then with a suitable pump stick set the edge well to the upper leather; so that the print of the stick may be visible on the edge of the sole, and pressed close to the upper leather; then wipe the paste clean off, and slick the edge dry; but if you should feel the stick adhere or stick to the edge of the sole, damp it with your tongue. When you have done with the edge, let the sole be slicked or buffed as custom or order shall direct; and the heel be finished as in that of the shoe.—When the last is out, clean the seat of the pegs; let the inner sole be made smooth in the fore part, and the upper leather laid close to the edge.

Channel Pump.

The stuff is to be fitted as in that of the shoe. The inner sole is to be laid to the last, and the seat of the heel rounded and holed as that of the shoe or pump.—The inner sole at the fore part is to be pared plumb to the edge of the last; and if it be stout enough, let it be taken off the last, and with the point of the knife slit the edge, near the grain side, round the fore part, in depth, full equal to the width of the sewing stitch, that, when the channel is sewed, it may cover the stitch: therefore it must be turned back when sewing.—But if the inner sole be too thin, you must cover the stitch with a thin strip or a sock: the latter is preferable to the other two.—Now lay the inner sole again on the last and last the upper leather, like that of the shoe; but the upper leather must be allowed wider than that of the shoe, that the tacks may be more within the inner sole.

After the channel is lasted, and the upper leather laid smooth on the inner sole, as well as the upper leather side, so that the edge of the last may be discernible, then brace the upper leather to the inner sole, close and firm, all round the fore part.

Then fill up the vacant space of the inner sole, that is between the upper leather, with some skivings to make it level, and proceed with the heel part as directed in the shoe. Before you put on the sole; put some paste between, and then let the sole be well settled, and round it nearly to the edge of the last; then go on with the heel to that of paring, before you proceed with the fore part.

When you have done so much to the heel, cut a channel in the sole round the fore part, about the same distance from the edge of the last as that of the sewing stitch of a pump; and the channel must be of such width as to have a skiving off of the grain of the sole, equal to the width of the stitch: in this case, the thread will be rather full.

Then, with a straight flat awl, hole the sole through and inner sole to the last, in the channel round the fore part.—Now take the last out, and make a full thread; let it be well waxed, but not so hard twisted as in that of the shoe. You must have two threads, one from the heel to the toe, and the other from the toe to the heel.—After you have sewed the channel pump round, put the last in again and fittings, and lay the sole even, and scour out the sole, and slick it well.—Then pare the sole to the edge of the last, like that of the pump, and pare it sloping from the stitch to the edge of the sole, so that the edge may be what thickness

you please, and slick the stitch, the sloping, and the square edges well; prick the stitches; and buff the bottom.—Now finish the heel as directed in that of the shoe.

A double channel pump is only to add a second row of stitching within the first.

Channels are, I believe, entirely out of wear, or nearly so. They are very stiff heavy wear, and it is very likely that they never will be in general use again.

A Man's Boot.

The fore part of a boot is to be made the same as that of the shoe; but for the heel part, instead of rounding the inner sole, as that of the shoe, you must pare it plumb without any feather, and nearly flush to the edge of the last; then hole it rather below the half of the substance of the inner sole, and the number of stitches to be full as many as in the fore part.

In lasting the boot, you must be particular that the heel-seam is even, and that the side seams are at the same distance from the toe; and that the boot drops or bangs free and, easy. In sewing, begin with the heel part, like that of the shoe, and let the sewing thread be well made, and in full proportion to the work. After you have sewed, lay the stitches smooth on the rand side, and pare off the loose leather above the stitch; but mind to leave as much as you intend the width of the rand is to be, including the width of the sewing stitch, and let it be laid down hard and smooth, that it may bear hard against the rand. Then turn over the rand, and brace it down firm and hard. Set the rand as near as you can to the form the heel is to be. That is, if the heel is to be square or sloping, the rand must be so likewise. For it would look very awkward to see the rand project beyond the heel, or the heel beyond the rand; therefore the heel and the rand should be level, that the work may appear one solid piece. Though we find some who call themselves good hands are not very attentive to the above directions.

Now, after the sole is put on and the piece sole joined, (which should always be lapped over, for the reason given in the directions for the shoe,) pare them round the heel within a quarter of an inch to the rand, and on the sole side settle them well down with the thin end of the hammer, and run round the rand the plain rand setter, which will put it in order for stitching.

The size of the stitching thread must be in proportion to the work, and with very little twist. Likewise the awl is to be in proportion to the thread, and flat like the stitching awl for the fore part; but more crooked. In stitching, be careful that the awl does not cut nor tear the sewing stitches. The number of stitches to be put in the rand, depends on the nature of the work, whether light or stout. Too many stitches in the rand is of more harm than good: about twelve stitches to an inch is sufficient for a boot of a middling substance. After you have stitched and laid the stitches down smooth on the sole side, put on the lifts; but let them be quite dry, as directed in the making of the shoe, otherwise you will not have a firm heel; and after you have pared them close to the sole, run a thin bone between the rand and the sole before you begin to hole the heel; and in the act of holing, be careful not to bruise the rand, for the heel is to be sewed down to the sole. Three or four lifts are enough to sew together at one sewing, and if the heel is to be higher, make a second sewing from the upper lift you have already sewed. After you have done sewing the heel and settled it, put a little paste on the rand, and scour the wax off the stitches with the rattle, but don't force the stitch too bare; then pare the sole sloping from the grain to the flesh side, and pean down the sloping part to bear on the stitches of the rand. Now pare the sole that is peaned to the stitch close to the stitch, and with the point of the knife take it off the rand below the stitch regularly all round the heel, without touching the rand: or, if you should not find your hand steady enough, you may run between the knife and the rand a thin horn, which will prevent the knife from injuring the rand: mind, in taking off the sole from the rand, that you do not take any more than the width of the rand is to be, and that you are to be governed by the nature of the work and the width of your rand iron. Now, put a little soft paste on the rand, and with the rand iron set the rand well, and when done, wipe off the paste clean. The rest of the heel is to be made as directed in the shoe. But always mind that the edge of the rand, next the upper leather, and the edge of the top piece are level; that is, if you put a flat ruler on the heel, that it will touch equally

every part of the heel, from the upper edge of the rand to the edge of the top piece. Then you have finished the heel as directed in the shoe, prick the stitches of the rand, and with a little gum water set the rand with a hot iron; but be careful that the iron is not too hot, otherwise it will burn the work and the leather: nor let the guides of the iron be too keen so as to cut, nor the back guide be too long to rub too hard against the upper leather. After you have balled the heel, let the iron be gently run over the rand. When the boot is taken off the last, let the seat of the heel be made smooth from all pegs and other roughness; likewise, the fore part to be the same.

Under this head I would wish to observe, (though custom has prevailed for many ages, with very few exceptions, never to make a boot without a stitched rand,) that a boot made with a good firm blind rand will be found in general to be better than a stitched one. By reason is drawn from observation and experience, for I find a stitched rand very often bruised and torn by the boot-jack; while the other stands the boot-jack without any impression being hardly made on it. But the heel and rand ought to be well made.

Cork Sole Boot or Shoe.

In making a cork boot or shoe, you must be careful that the cork is full as wide and as long as the last; then split the cork into two, as the common thickness of the cork sold at the cork-cutters is thick enough to split into two, for what is commonly used in boots and shoes.

After you have split the cork in two, round them to the last, level them, and reduce them to the substance they are required, and at the edge let them be a little thinner than in the middle; then round them to the real width they are to be: they should be but very little within the last, after allowing for the covering sock.—Now, to mould them to the last, let them be held to the fire by an awl or a fork, till the action of the fire causes them to curve or bend to the mould of the last; and you will soon discern when enough. Then round the inner sole as in any other boot or shoe, but mind that it be as wide as the cork. After you have rounded the inner sole, take it off the last, and put on the last the covering sock with the grain side to the last, (the covering sock should be of basil or calf skin; the shank of wax calf-skin is the best;) then the cork, and the inner sole on the cork, and secure them to the last, and be careful that they are all even and in their proper place. Then turn up the covering sock over the edge of the cork and inner sole, that, it may be sewed in. with the upper leather and welt.

Now, with the rest of the work you must proceed as in any other boot or shoe.

Woman's Wood-heel Pump, Calf, Spanish or any kind of Morocco Leather.

The stuff is to be fitted as directed in the making of the man's pump. Then you must dip the heels in water, if very dry; but if green you should put them to dry. But it would be better to dip the heels in water, and then put them to lie by while you are fitting the stuff, as the wood will cut the better. Then with your heel knife level the seat of the heel, and cut it round the seat to the seat of the last, and a trifle narrower; then, with the crooked knife, h&l the seat of the heel to fit the seat of the last; but mind, that the seat of the heel should not bear on the seat of the last quite to the edge, but within an eighth of an inch to the edge of the last: the heel should be full one eighth of an inch above the edge of the last, which will nearly be the depth of the sewing seam; for you must observe, - if the seat of the heel is made to fit the seat of the last close all round, that when you have sewed in the rand, and put in the heel, the edge of the heel must rest on the sewing seam, which is about an eighth of an inch high, and the middle part of the seat of the heel will be hollow from the inner sole; which will render the heel neither smooth nor firm, but liable to break at the sides in the wear, if not in the work.

When you have done with the seat of the heel, cut the top piece so, that it may lie level with the tread of the last at the joints; that is, when the seat of the last is put to rest on the heel, and the heel and the last put to rest on a straight flat board; and if the whole of the top piece and the tread of the last at the joints bear in every part on the board, then the top piece of the heel is cut to answer the tread of the last. Then form

the top piece to the size and form you intend it to be (but I would have you to let the top piece be more wide than long if it be a peg heel; but if a court heel, otherwise), and from the edge of the top piece that is to be, cut, the heel down to the small, and from the small to the edge of the seat; but mind not to cut the heel too thin at the sides, for, if you do, they will be liable to break. Likewise mind in cutting the heel down in front, that you do not thin the shanks too much, otherwise they will break.

In hollowing out the front of the heel with your crooked knife, let it be so hollowed as to leave an edge to the side of the shank from the top piece to the end; but do not hollow the middle of the front too much, that the heel may not be too weak. After you have done with the knife, take your flat and half-round file, and file the heels smooth. Now, as you have got the stuff and heels ready, you must proceed as in that of the man's pump; but mind to paste the linen socks on the inner soles, and mould them to the last, and put them to dry in the sun's rays, or before the fire, that they may be perfectly dry before you use them. When you have turned the pump and got it ready for second lasting, cover the sock with some clean paper before you put the inner sole to the last, and after you have put the inner sole to the last, and pared it close all round, put the heel on the inner sole at the seat of the last, and let it be fixed there in its proper place, that is, about an eighth of an inch under the last; and with the point of the knife mark the inner sole close to the edge of the seat of the heel all round the seat of the inner sole, and with the back of the knife mark the inner sole across at the ends of the shanks. Then take off the heel, and with the point of the knife mark off within the first mark (if the inner sole be stout enough) the width, equal to the substance of the quarter, lining, and heel rand; then feather the inner sole from the first mark to the edge of it; and let the feather be as wide as will keep the quarter (when the pump is off the last) flush with the edge of the seat of the heel. Here the real width cannot be ascertained, but must be left to your judgement to direct according to the nature of the work, whether it be stout or light. Now with a crooked sewing awl of a suitable size, hole the inner sole all round the seat, from the inner mark to the first.

When you have done with the seat of the inner sole, round the fore part at that distance from the edge of the last, as, when it is put into the fore part of the pump, that it will fully cover the sewing stitch, and skive it thin at the edge round the fore part of about the width of the sewing seam of the pump. The next thing is to put the shank piece on the inner sole, and the broad end must be put under a skive cut on the inner sole just under the rise of the last at the joint, and a tack in the other end, at the seat; but always mind to put some paste between the shank piece and the inner sole. Put a small peg in the inner sole at the toe, and give a short slit in the inner sole from the peg inward, that the peg may come out with the last, when it is to be taken out of the pump: then

some paste on the fore part of the inner sole, and put it with the last into the fore part of the pump, and be careful that it is even, that the last is not more over one side than the other. Put a tack through the sole and inner sole into the last in the waist or small, and take up the quarters; secure them at the heel seam with a small tack, and be careful not to sink them too much, that you may sew off no more than what is sewed off of the quarters in the fore part; otherwise the quarters are liable to be too shallow, which will disappoint the cutter as well as the wearer. Now settle the sole, and put a cover over the upper leather to keep it from dirt or rubbing; unless it be common leather: in that case there is no need of it. Now put the heel rand (previously damped with water) round the heel, with the grain side to the heel, that you may not soil it with your fingers, if it be any kind of morocco, and mould it close to the heel; then take it off the heel, and cut it close to the mark that the seat of the heel has made on the rand; slit each side of it at the hollow part of the front; likewise cut off the end of the rand that you are to sew first with, at the mark that the end of the shank of the heel has made. In sewing the rand, let the first and last stitch come over the ends; and take only a sufficient hold in the rand, that it may not tear out, and no more. When that you have sewed the first side nearly to the heel seam, pare off the loose leather that is above the stitch near to the stitch, and with the hammer of the pincers lay the seam down smooth; and from the heel seam out nearly to the other end you must pare it every two or three stitches.

After you have fastened the end of the threads with a knot, or a stitch in the insoles, let the rand be set smooth and even; but before you put the heel in, let it be lightly waxed or pasted. If the former, which is the best for calf-leather pumps, you may put a little paste over the wax, at the hind part of the heel, that it may slip in freely. When the heel is in the rand, mind that it is even in the scat, and that it bears equally on the edge of the rand; then fasten it to the last with a tack through the front of the heel.

Now let the pump be held fast on your knees with the strap, by letting the strap come up between your knees over the pump; then with the pincers pull up the heel rand over the top piece, and put two or three tacks in the rand on the top piece, and last the rand in front of the heel; but mind that the two first tacks are put to strain the heel rand on each side of the small of the heel.

After you have lasted the rand to the heel, and if the rand be brown calf-skin, let it be coloured black, (and likewise the upper leather being black,) and scour it out with some paste. Then set the seat of the rand, and slick the rand well. All this is if it be calf-leather: but if it should be morocco of any colour, you must be careful to keep the rand clean and not soil the colour; and if it should be kid, it should be sewed in with a lining, as the kid is too weak of itself. Now secure the heel firm with the heel stay, and mind that the heel stay is long enough to clear the quarters from the tacks; and if the heel rand is of any kind of coloured morocco, &c. put some paper between the heel stay and the rand. After you have secured the heel firm with the heel stay, brace the rand in front of the heel, and as you proceed in bracing, take out the tacks; but that part of the rand which is on the top piece you may pare off.

Then with the long stick slick it smooth in front, and with the half-round file, file the shanks both sides from the ends to the top piece lightly at the sides, that you may have an edge to the rand on each side.

Now if there should be any vacant space between the heel and the inner sole (which should not be, according to the directions given for cutting the heel), fill it up smooth with some skivings and some paste.

Then let the shank piece be laid up the heel smooth with some paste; and if there should be any vacant places at the ends of the shanks, let them be filled up with some skivings and some paste, that the whole may be smooth and even: then cramp or fold in the sole full as much as the hollow front of the heel requires, and secure it with a tack in front of the heel between the top piece and the small of the heel; then with the cramping hammer lay the cramp in close and smooth, and with the long stick slick it in well.

When done slicking of it, pare the sole round each of the shanks close to the edge of the rand, only leave as much space as you think will cover the stitching stitch, and thin the sole in front of the heel to the substance the work requires the edge of the shank of the sole, to be.

The roughness at the edge of the sole round each shank is to be taken off by running a thin horn between the knife and the rand, round each shank; then take the tack out that is in front of the heel, and put in a peg in its room, and with a knife level the sole even in front of the heel, and slick it down well; then cut the channel on the sole each side of the shank, at that distance from the edge that the nature of the work requires, and the width you intend the shank to be.

The top piece may be secured with one or two tacks, as the width of the top piece requires; but in rounding of it, let it float so as to have the same regular sweep or curve as the heel has from the small to the top piece, and leave the same distance from the edge of the top piece to the heel rand, as you have left to the shank, so as to cover the stitching stitch. Likewise round the top piece in front of the heel, so as to have that gradual sweep of the hollow 'of the front, and the corners with that of the shanks, and the channel in the top piece must be cut to answer those of the shanks.

The stitching thread must be in proportion to the work, whether it be made of flax, spinnel, &c. and two threads must be made, one for each shank; that which stitches the first shank should be long enough to stitch the top piece too. The stitching awl should be round, and nearly of the same size, for the whole length that is used in the work, except at the very point, which should be rather flat.

Let the stitches be regular, and as near the edge as you can, with the proviso that the bold is firm in the rand. The number of stitches depends on the nature of the work and the size of the thread, but the number to an inch is about twenty to a morocco pump.

When you have done stitching, take the tack from the front of the heel and the top piece, and put pegs in their room; then close the channel, and with the cramping hammer lay the shanks and top piece smooth and even, and slick them down well. With the thin end of the hammer turn the edge of the top piece next the stitch over the stitches. In the rounding up of the sole at the shanks before stitching, it was directed that it should not be left wider than would be needful to cover the stitch; but if it should be more after stitching, it is better to pare it off just so as to cover the stitch, that you may make the shank to a certainty. Then thin the shank from the channel to the edge of the sole that covers the stitch; but let it be so gradual from the channel to the edge, that the leather shank may be firm in the middle, and only thin at the edge: though the work should be ever so light, and the shank appear ever so thin, the shank should be left so firm in the middle that the edge may rest firm on the stitch.

After you have pared both shanks to the substance you intend they should be, take the half-round file, and file lightly the shanks to take off the roughness of the paring of the knife, and scrape off the roughness of the file with a bit of glass. Then damp the shanks, and slick them well with any kind of long stick; but if you wish the shanks to appear of a darker colour than that of slicked leather, make use of a long stick made of red sanders wood, or let the wood be rubbed with a little water on a stone, and it will give a colouring for to stain the shanks with before you slick them. But never be fond of daubing the shanks with a quantity of red earth of any kind; for it will look dirty, and will deform the work.

When you have done slicking the shanks, pare the top piece, and be careful that it does not float too much over the heel, nor too little; for in either case it will appear unsightly: it should be pared in a line with the sweep of the heel from the small to the top piece, and likewise the front; then there will be a proportion between the whole of the work.

Colour the edge of the top piece black if the upper be black, or any dark colour; but if white, or any light colour, let it be of the brown colour of the leather, well slicked.

In slicking the edge of the top piece, mind that the shoulder stick is of the same angle or float with the top piece, that it may bear or press equally on every part of the edge of the top piece.

After you have slicked the top piece, take the thin horn and run it round the two shanks and top piece between the stitches and the edge, to rise the edge of the two shank a and top piece a little from the stitch. Then at the end of the shank on the left hand side put the horn between the stitch and the edge of the shank, and with the point of the knife pare off from the edge of the shank as much of it as does cover the stitch; the knife to be held sloping inward, that the outward edge of the shank may rest on the back part of the stitch without any space to be observed between the stitch and the edge of the shank; and the same for the two shanks and the top piece. Now take a piece of clean linen rag, and wrap it round the end of the thumb of your right hand, and damp that part that is inside of the nail with thin gum water, and run it round the edge of both shanks and the top piece. At the same time you may clean the stitch, if it should be dirty, with the dry part of the cloth that is on the back part of the nail.

Then prick the stitches, damp the shanks and slick them down well, rid the edge of the top piece; but be careful not to rub the stitches of the shanks. In the next place level the sole in front of the heel with the knife, file, and glass, and slick it well, and the top piece. Now you come to the fore part, which is to be managed the same as directed in the making of the man's pump. But here, as well as there, you must be careful not to pare the the edge of the sole under the sewing stitch.


When you have done with the edge of the fore part, slick and buff the sole as your fancy or the fashion of the time directs. Then take off the heel stay, clean the rand and slick it, set the seat of the heel rand, and stamp the tack holes. After the last is out of the pump, lay down the feather of the inner sole to the seat of the heel, and the tipper leather close and smooth to the edge of the fore part of the sole; rub down the tack holes, and strain the pump so that the quarters may sit close. and smooth, and put it to hang on a nail to

dry before you gum the heel rand.—When you think the rand is dry, gum it lightly over with the middle finger of your right hand; don't put too much on, but do it over quickly.

Woman's Wood-heel Pump, Silk, Stuff or any wove Upper.

The bottom stuff is to be fitted the same as in the leather pump. The heels to be cut the same, and the rounding of the sole.

But in lasting the upper you must be more careful than in that of the leather; for, if you do not have the lasting tacks on each side in a direct line from the top of the quarters at the heel seam, and along the side seam, with the threads of the vamp to the lasting tack, as from A. to B. in *fig. 1st*, and so on as directed in the man's shoe, you are not to expect to have the upper smooth.

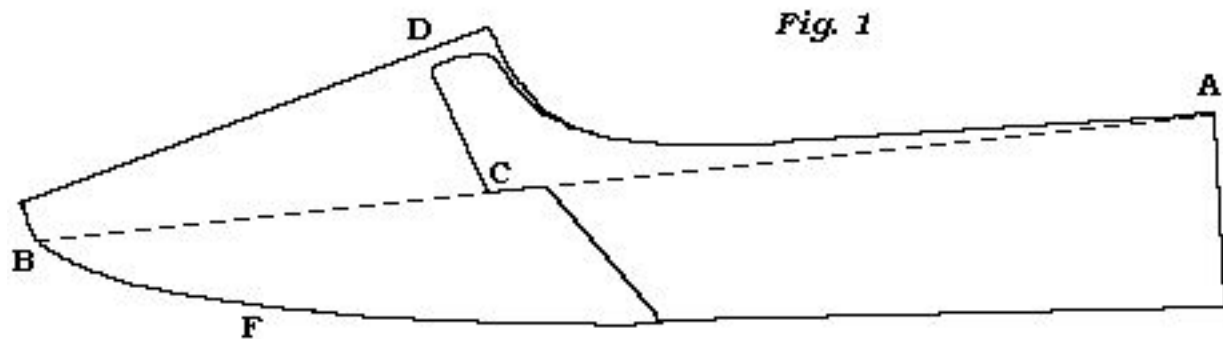

The sewing thread must be made in proportion to the work, and the bristles must be pointed; otherwise you will not be able to get them through the upper.

Likewise the thread should be kept the same as directed in the leather work; though it does not require so much wax.—When you have sewed, cut off the spare lining and side lining that are above the stitch; but mind not to cut off the spare lining that is above the stitch, but wax it down to the sole.—From this you are to proceed as directed in the leather pump, till you come to the heel rand.

The heel rand has in general a linen lining; but to silk, thin white sheep-skin is best.

Damp the linen lining with your tongue towards the upper part of it, that it may close to the small of the heel, and put the heel on your Left knee, with the hind part towards you; then put the lining over it, and with the fingers and thumb of both hands work it well round the heel, and take the heel and rand tip between the fingers and thumb of your left hand, and mark the rand round the edge of the seat with some colouring, and mark the middle behind at the seat, and likewise at the small of the heel, and at both sides, where the threads from the small of the heel run down to the seat.

Now take the lining off the heel, and cut off that end which you are to begin to sew with close to the mark, which is the right side.

In fastening the lining to the heel rand, some make use of paste, and others of wax; and I think that, for stuff, the wrong side of the rand slightly waxed is best, and paste for every other kind of wove rands.

In laying the lining on the rand, some will put a plait or fold at the top piece part of the lining, for to strain the rand sufficiently close round the small of the heel, when it is in; but I would have you to lay the lining flat on the rand, and strain it at the shank ends on each side, that it may lie smooth on the rand.

Then put them on the seat, and sit on them while you are second lasting the pump, that they may stick firm together.

When sewing the heel rand, mind to sew in the mark that is made on the lining, except within two or three stitches of the mark that is made in the direction of the threads that come round the small of the heel, on each side; let the hold be there about a quarter of an inch below the mark; and two or three stitches after you have passed that mark, as well as before you come to it; and the same on each side.

This mode will answer better than a plait or fold in the linings as it will strain the heel rand enough in the small of the heel, and will be quite free at the top piece; but in the mode of the plait or fold, it will cause the heel rand to strain too much at the top piece, which will be found very unpleasant in a middling or low heel.

And while sewing, you are not to pare any off the stitch as in leather, but to lay the whole down smooth with the hammer of the pincers; and if the heel be middling high, you may sew to the heel seam before you begin to hammer the seam down; but in a low heel rand it must be done sooner and oftener.

After you have sewed the rand, and before you put in the heel, put in a thin leather slide full as wide as the seat of the heel, for to cover the spare rand, lining, and stitches, to prevent any of them to rise up against the edge of the seat of the heel when putting of it in.

If it be a stuff rand and waxed, put a little paste lightly between the rand and lining, that they may slip by each other with more ease, when lasting the heel rand; and before the heel is put in, put a little paste over it.

Now put the heel in, and let the seat of the heel cover the sewing stitches equally all round the seat of the pump. Then take out the slide, and secure the heel in front with a tack; then place the pump on your knees under the strap, and draw up the lining over the top piece, and see that it is smooth all over the heel, and then the heel rand in the same manner.

Now you have the rand over the top piece, lay it in front of the heel, but first let it be well lasted in the small, as there is the principal part of the lasting in all kind of wove heel rands. All the rest is the same as directed in the last article, till you come to stitching.

Then for stuff and velvet you must make use of covered stitch; that is, you must stitch with one thread, and that thread when drawn in from the sole side must come through the stuff or velvet rand, but when drawn out at the sole side, must go over the rand, and so alternately through the whole of the stitching.—But should the heel rand be silk, jean, or nankeen, you may fair stitch them the same as leather, and finish the whole of the work the same as if it were leather.

The over stitch work must be covered by the shanks and top piece, and the form of the shanks is to be the same as in stitch work, without any alteration except that of covering the stitch.

I suppose that the reason is evident for making use of a covered stitch in stuff and velvet heel rands, on inspection: for in the first you can't rise a regular hold; and the threads are liable to fret by the friction of the stuff; and in the velvet the stitch will be buried in its plush.

But in silk, jean, or nankeen, you may use fair or covered stitch.

The rest of the work is to be finished the same as directed in the last article.

Woman's Shoe, Leather, Silk, etc.

The bottom stuff is to be fitted the same as dissected in the man's shoe, except the hind part of the sole, which in must be partly thinned as directed in the woman's pump.

After you have fastened the inner sole to the last and rounded it, let the feather of the fore part of the inner sole be something wider than the substance of the upper, lining, side lining, and rand; but not wider than what will keep the upper down smooth on the edge of the rand, when the last is out.

Unless the shoe is what is commonly called a blind welt, then the feather must be similar to that of a man's shoe.

The heel part you must proceed with, the same as directed in the pump.

After you have holed the inner sole, and lasted the shoe, prepare the rand, which should be about half an inch wide, of middling substance and mellow leather; but if you should find it rather stiff and hard, put it between your knee and the edge of the knife, with the back of the knife inclining towards you, and skive off the grain of the rand.

By drawing the rand twice or thrice under the knife in that position, it will become pliant enough.—You must sew the fore rand as directed in that of the boot rand, and proceed in a similar manner till you have braced it.

When you have braced the rand, level the inner sole to the rand with some skivings with some paste.—The heel part you are to proceed with as directed in the pump, according to the kind of work it is of.

Now. put on the sole, and round it so close to the fore rand as to leave only enough to cover the stitch; and cut the channel as in the man's shoe.—The stitching thread must be according to the quality of the work, black or white, full or small; but let it be what it may, the form must be the same.—Unless the work be very heavy, the threads are white made of flax, spinnel, &c. The awl must be round: the number of stitches is according to the nature of the work and the fullness of the thread.—The hold is to be near the middle of the rand; but you should prick the rand at the place where the stitch is to be, before you take the hold.

After you have stitched, close the channel, scour the sole out, and slick it well: then with the train end of the hammer turn the flesh edge of the sole over the stitch.—Now pare the sole square at the edge, and nearly close to the stitch; and if the upper be black, colour the edge so too; but if of any other colour, let the edge of the sole remain the colour of the leather.

With a little soft paste damp the edge of the sole, and with a suitable shoulder stick slick the edge well all round; then with the point of the knife take the loose leather from off the stitch, as directed in the top piece of the pump.—Clean the stitches and prick them; then clamp the edge of the sole with a little gum water, and with the shoulder stick slick the edge well, all round, and set the rand.

The heel part must be finished the same as that of the pump, and the buffing or slicking of the sole, as well as the inside part when the last is out.

Woman's Cork Shoe.

The cork is to be prepared the same as directed in the man's cork shoe; only, instead of thinning it at the edge, you must leave it nearly of the same substance at the edge as it is in the middle, and square; but that part that is to be towards the heel must be taken thinner.

After you have fitted the cork, you must proceed the same as directed in the last article; only the rand must be wider in proportion to the thickness of the cork.

When you have sewed the rand in, and pared the spare leather off, that is above the stitch, &c. fill the vacant space that is near the sewing stitch with some skivings with wax, to level the sewing seam with the middle of the inner sole; and wax the inner sole and sewing seam before you put the cork on.

While the wax is warm put the cork on, and see that it covers the sewing stitches regular all round, and secure it to the last with tacks.—Before you turn the rand over the cork, see that it is even, and square, and waxed; then turn the rand over the cork, and brace it; and proceed in every other respect as in the last article.

Woman's Cork Pump.

The cork is to be prepared. the same as in the shoe, only the edge of it must be taken down thin, and no wider than the inner sole of the pump.—When you have prepared the inner sole for second lasting, wax the cork to the inner sole, and turn the sock over, which must previously be left, wide enough, and brace it firm over the cork; then wax it over before you put it into the pump.

But mind, when lasting the pump, that you make proper allowance for the cork, otherwise you will have the pump too narrow.

A Turnover Pump or Shoe.

The fore part of a turnover, whether it be a pump or a shoe, is to be made the same as directed under those respective heads. The inner sole of the heel part must be pared full to the edge of the last, and a feather left to it full as wide as the substance of the quarter, lining, and rand.

When sewing the rand, let there be a thin slip of leather or cloth sewed in between the rand and the stitch, as it prevents the rand when turned over from grinning. After you have sewed the rand, pare the spare leather off that is above the stitch, and lay the seam smooth; but if it be any kind of wove stuff, you must not pare it off, but lay it down smooth with the hammer or pincers.

Now, if it be a spring heel, you must put on the split lift and lift before the sole, and proceed with it as directed in the man's shoe. Some do sew the lifts as in the man's shoe, and some secure them with pegs; the latter will answer, if secured well. Let the heel be of a gradual slope from the hind part to the corners, and there diminish next to nothing.

Before the rand is turned over, put some paste between the rand and the heel, and last the rand on the lift, and brace it down firm.

Then set the seat of the rand, and bring the sole over, and proceed in the same manner as directed in the top piece of the woman's pump. But if the heel is to have a top piece instead of a spring sole, the sole is to go on the sewing stitch, and the heel to be made square in front, as well as at the sides, before the rand is brought over.

Women's plain Heel.

The Woman's plain heel, whether a pump or a shoe, is to be done in the same manner as directed in making of the heel in the man's shoe or pump.

PART II (Cutting)

Men's Shoes.

But before you begin to cut, you should learn to take the size of the foot, and the orders relative to the shoe: therefore take the size stick, and let the person's foot lie flat on it, with the fixed upright close to the person's heel, and the sliding upright close to the longest toe, and that is in general the great toe; then you have the real length of the foot,—Now, to put the length of the foot down in the order book, you may put the bare length, without any allowance, as some do; or enter it down with the requisite allowance the last is to be of the latter I would have the young learner to adopt; as it will do away any further thought, when you are to look for a last to cut the shoes out.

In the next place, with a graduated piece of parchment, taken from the sizes on the size stick, or graduated in any way so as to be a fixed rule, take the width of the foot over the instep, and over the joints of the toes and set them down in the order book.

Then take the length and depth of the quarter, the width of the sole at the joints, and the form of the toe, the quality of the leather, whether it be wax or grain calf-skin, seal or Spanish light, middling or stout, all of which enter in the order book.

In bespoke work there may be many more trivial orders given, which depends on the customer's opinion and fancy.

I mentioned above, that you must make such allowances in the length of the last above that of the foot, which of course I should explain.—If you ever worked on the seat, you must have observed, after a shoe was taken off the last, and left to dry a day or more, that it was not possible without violent efforts to force the same last into the same shoe again.

Because leather is of an elastic nature, and it is strained on the last in the making of the shoe, as soon as the last is out, it endeavours to regain its former position; therefore the shoe will get smaller: and independent of that, no person would be able to bear a shoe so tight as the shoe is on the last.

Therefore, experience has taught the trade to make certain allowances according to the form of the toe.—Hence, for sharp toes, three or more sizes; for round toes, from a size and a half to two sizes: but if the toe of the last is very full, and rather thick, from half a size to a size.

These allowances are for a middling size foot; but if the foot is slender, you may not allow quite so much; and if fuller, you must allow something more. —To write the whole of the order in words, would take too much room and time, besides being prolix to look over. To abbreviate these inconveniences, I shall give for an example the following formula :—

Mr. Timothy Trusty, No.

Piccadilly,

7 4/3., W, G, S, or Span. Shoes or Ps. Qr. 6 1/2. D. 2 1/4, S.
or R. toe. Bot. 3. light or
stout. R and L.

The above in words.—Mr. Timothy Trusty,. No. Piccadilly. Foot seven sizes in length, four sizes over the instab, three over the joints of the toes, wax or grain calf leather, seal or Spanish leather. Quarter six inches and a half long, two inches and a quarter deep, sharp or round toe, bottom of the last at the joints three inches wide, light or stout, right and left lasts.

A. bare inspection, of the two is sufficient to give a decided preference to the first.

Likewise. you must pay attention, whether the person has a thin or full heel, a projecting or a dented heel behind, and whether a flat or a hollow tread to the foot: these things you must observe, that the last may be similar.

In choosing a last for the customer, endeavour to recollect the person's foot, that the last may be as near alike as you possibly can, and you are to pay every attention to the customer's orders; but though I would have you to be regardful in every respect to the orders of the customer, do not forget the shoemaker; that is, don't let him lead you from the trade, which has often been done to the disappointment of both.

If the last should be a block last, and with it boots have been made to fit the person very well, you are not to trust to it on that account to make shoes on it for the same; because they will be too narrow.

In a boot, the vamp is in one piece from the ankle to the toe; therefore it will give way to the foot with more ease and freedom than the shoe; because the side seams in the shoe will not give way, but will girt the foot too tight if made off the same last.

Therefore, as the side seams will not give way for the foot as the vamp of the boot, you must make use of a middling instab leather on the last to obviate that defect. I mention this circumstance, that you may not take it for granted, as the last served in one instance, that it must do in the other; but that you may be on your guard, to pay attention to the directions taken.

Hence it is evident, that the foot of the boot, to fit close about the instab, may be a full size less than the real measure of the person's foot.

Another thing I would wish the young learner to pay attention to, is, that the spring of the last is full equal to that of the foot.

You must have observed, when taking the length of the foot, that from the first joint of the great toe, to the end of the same, that the part of the foot gradually inclines above the flat or level of the size stick, and that the toe bears in general against the sliding upright from an inch to an inch and a half above the flat or graduated part of the side stick.

Therefore the last should be full as much of the same spring; otherwise there will be more upper leather from the top of the heel seam to the toe, than the length of the foot in the same direction, and consequently the quarters are very liable to sit loose.

Now, after you have chosen a last to answer the purpose, you must prepare the patterns*, before you can attempt to cut the leather.—Let the patterns be of middling stiff paper, which is generally used, as being easier formed and altered.




*I would not have you to hanker after old patterns from this or that shop; but to form in your own mind such patterns as circumstances may require.

In the first place, cut the quarter to the length and depth, and the upper part to the form required, as some require it high behind and low at the side, as sailors usually do; others rather straight from the heel seam to the tie; and some high at the side and low behind; but a projecting heel must have the quarter rather high behind, otherwise it will be inconvenient to keep the shoe on the foot.—These things you must be attentive to, when the orders are given.

The general mode of the form of the quarter at the upper part is rather straight, and the strap at the tie about half an inch wide. The form of the quarter at the side seam you must leave till you have fitted the vamp pattern to the last, which you must leave so much fuller than the last as you think will taken up in the sewing, and that is about three-eighths of an inch to half an inch. Or, as much as you think is needful from the edge of, the last to cover the feather of the inner sole, and to come under the sewing stitch.

Then fix the quarter pattern on that of the vamp, and lay the last on them, and see that the heel seam part of the quarter is regular with the middle of the heel part of the last; which should have been cut in the first place to answer the heel seam part of the last, for the last is fuller at the low part than at the top of the heel seam, to answer that of the man's heel: therefore the heel seam part of the pattern ought to be cut sloping, to correspond with the heel part of the last. Now that you have the heel part of the quarter and last to answer, look to the vamp at the toe, and let the middle of the vamp come full over the middle of the toe of the last; for so much as the middle of the vamp is above the middle of the last at the toe, so much will the upper part of the upper leather be shorter than the last in the same direction: therefore it is sufficient for the middle of the vamp to be a trifle above the middle of the last at the toe, to give a proper strain to the quarters and vamp: likewise, leave the vamp so much larger than the last, as was observed before, that it was to be wider.

Now take the last from off the patterns, and let them remain in the same position with a weight on them; and before you cut the form of the quarter at the end of the side seam, whether it be as that in fig. 1st, 2d, or 3d, the distance from A to C, and front C to D jointly, must be equal to half the width of the heel, taken to the rising part on the back of the foot; otherwise, the person for whom the shoes are made will not be able to get the quarters up at heel.

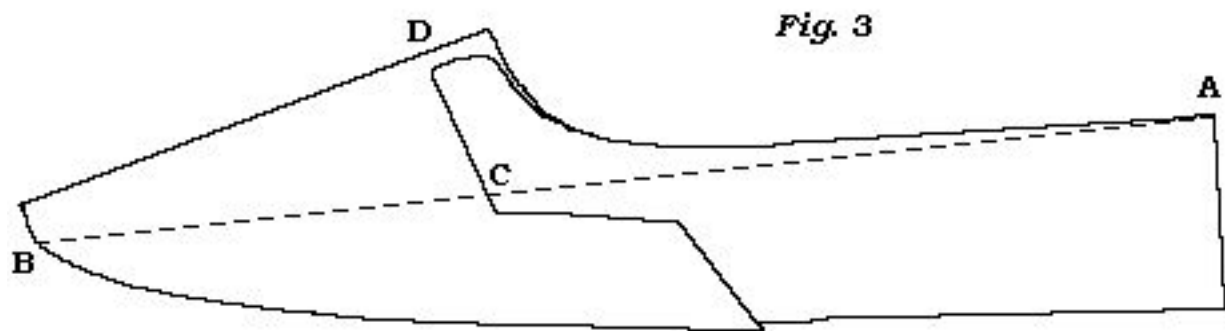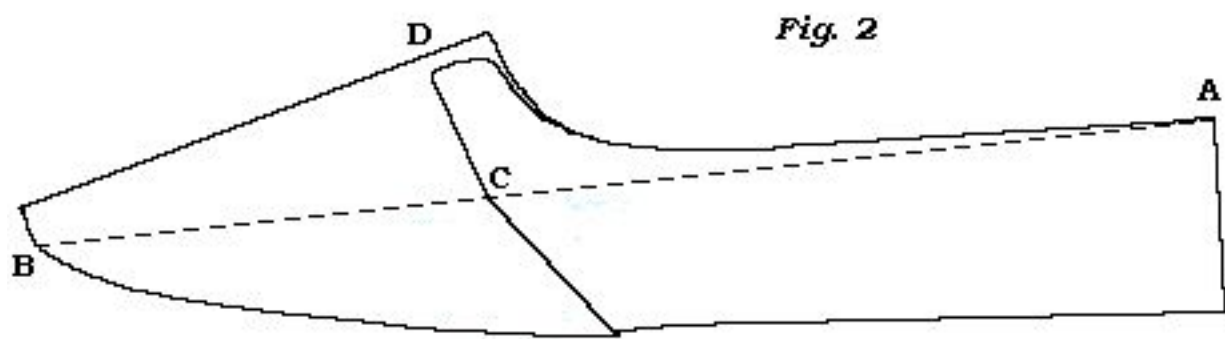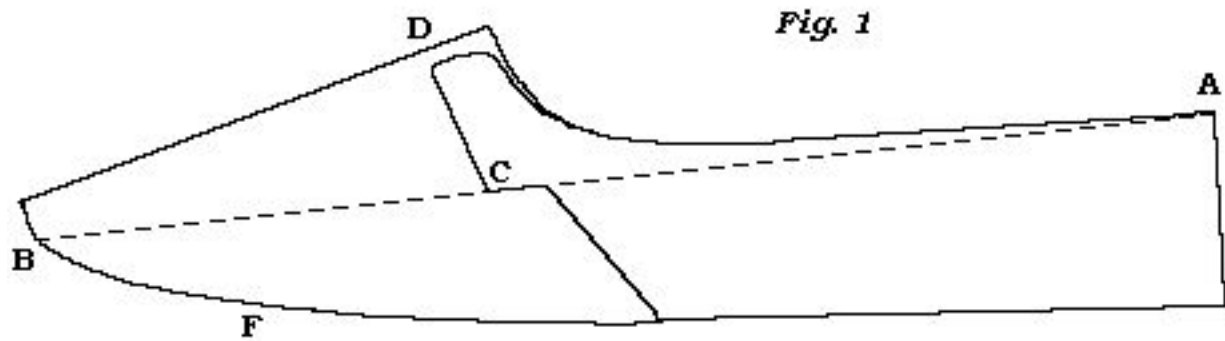

Therefore, in a very short quarter, you must mind that the length from the heel seam to the stabbing at the side seam, and from thence to the middle of the vamp under the tie or strap, be equal to half the length of the heel, as above described. Hence, unless there be heel room, the shoe will not get on the foot.

From the above it is evident, that if the quarter be short, the side seam must be low in proportion, that the length from the end of the heel seam to the stabbing at the side seam, and from thence to the middle of the vamp under the tie, may be equal to half the length of the heel as above: so the distances on both sides are equal to the whole length of the heel.

But if the quarter be long, that is, seven inches or more, then it is beyond the length of most men's heels; the above rule is of no consequence in this case, for here you are to let the side seam be as high as the decent appearance of the shoe will admit that the stabbing at the end of the side seam may clear the joints

of the foot, which you can in the form of fig. 1st, and 3d; but in the form of that in fig. 2d you cannot avoid it so well.

Now, after you have taken the dimensions as above directed, mark the height of the side seam with the point of an awl, and cut it to one of the above forms, and let there be a sufficient length of the vamp come within the tie: but that depends much on the fancy of the customer, as some will only have it barely within the tie, and others will have it half an inch or more: so in this case you must be guided by the customer.

In all of the above three forms let the side seam be cut sloping inward towards the heel, not only, if the quarter be long, to avoid the seam from pressing on the joints, but it will give the shoe a free and an easy appearance, and will be much stronger, as the strain is not so great in an oblique as in a direct position, (and by Mechanics, it is, As the Sine of the Obliquity, is to Radius.)

In like manner you must proceed with the patterns for every customer; and for general use, you may cut patterns to every size last, and to every length and depth quarter, and to narrow, middling and wide vamps, such as you may think and find in your daily practice, that will become in constant service.

Now as you have the patterns ready, the next thing is to trench by them the upper leathers out of the skin.—But before I proceed, I would wish to draw your attention to an observation or two on straight and crooked lasts.

Right and left lasts are made as near as possible to the form of the feet, and the shoes made on them will fit better than those that are made on straight lasts. —The right and left shoes have no loose leather at the inside of the feet when they are on, which is unavoidable in the straight: but there is one great disadvantage in the right and left; if the wearer do not tread even, the shoes must wear much on one side, as there is no remedy in changing; to which some persons are very partial.


Some people have the soles of their feet very flat, and they find right and left shoes very uncomfortable; therefore in this case a straight last is preferable.—Likewise persons whose feet have been tortured with the gout, rheumatism, or violent corns; for all of them give the preference to a straight last.

To obviate as much as possible the uneven tread of the wearer of a right and left, let the inside ball of the last at the joint be higher than common, that the inside joint of the foot may be thrown to bear, heavy on the inside tread of the shoe.

Now we will proceed to that part which is commonly called

Trenching.

Here I would have the young tyro to be particular, at all times when trenching, to let the length of the quarter and width of the vamp be in the length of the skin; as: you may observe in fig. 4. I have only marked out half of a skin, as the other half is to be cut in the same order; for the two vamps must be cut to match, one from each side of the skin directly opposite to the other, otherwise they will be of unequal substance and texture.

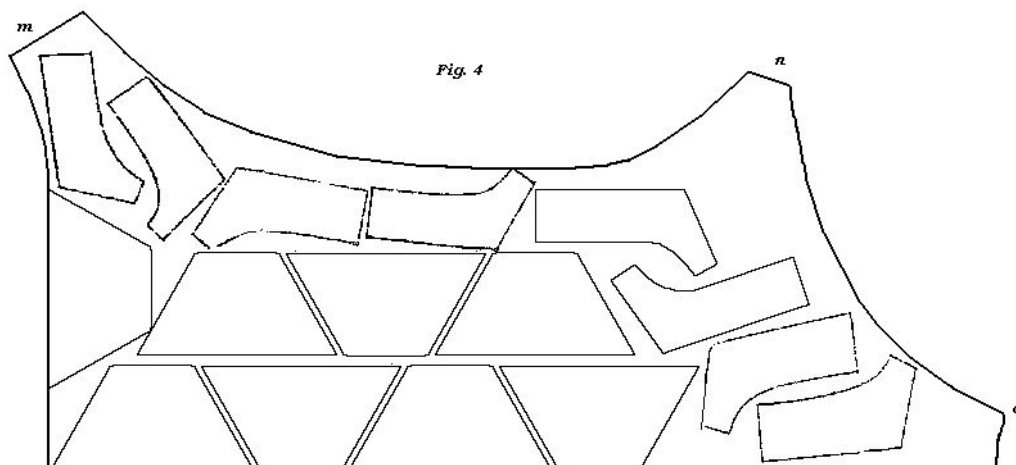

If there should be a defect in the opposite side of the skin, that will prevent you from having them out direct, let that on the defective side be as near as possible, that the two vamps may be similar in substance and appearance for to wear alike.

The quarters are not of that import which the vamps are, for they are not exposed to the wear the vamps are; they may be taken out of the shanks, as at *m*, *n*, and *o*, if the leather be of proper substance and fineness.

The reason that I would have you cut the skin in the manner above directed, is, that all skins have the fibres running lengthwise from the head to the tail and down the legs; therefore the strongest way of the skin is in that of its length.

Indeed, a skin is not much unlike that of a piece of cloth; for the fibres of the skin of an animal are like the warp threads in the loom, which constitute the length and strength of a piece of cloth; for the woof (or the threads carried along with the shuttle) is to bind and keep the warp threads in the form the cloth is to be of; and hence it does not constitute its real strength.

Therefore, as a skin is similar to that of a piece of cloth, the strongest way is in the length or in the direction of the hair of the animal; but of woolly animals, such as sheep, the skins are not so regular, besides being very porous.

Now, to cut a skin to the best advantage, is to cut one skin into quarters of one length, and another to another length; and likewise the same for vamps. But as vamps cannot be cut good and fine beyond the shoulders of the skins for the shoulders and the necks are in general too coarse, they should be cut into quarters, boys' shoes or coarse men's shoes, which may wear equally as tough as the fine part.

After you have trenched the upper leathers out of the skin, take a pair of pincers and stretch the quarters in the length, otherwise you will not be sure of the length or depth of them; for some kind of leather will stretch a great deal more than others; and unless previously stretched, the quarters, when the shoe is lasted, may so stretch that one quarter may be a quarter of an inch longer than the other, and consequently shallower in proportion.

The vamps are to be strained in length, and fold them in the middle, the black side together. Cut the vamps and quarters true and smooth to the patterns. Let the vamp lining be cut out of strained sheepskin, or yellow rone, and wide enough to come on the vamp a little beyond the opening of the side seam, and long enough to come below the side lining.

On the vamp lining write the person's name for whom they are intended, and the length and width the last is to be of, that, if they should not fit, you may know the size of them when put in the shop.

Let the strap bits be of any kind of morocco leather; such bits as come off in cutting women's work. The back pieces and side lining, the form of them I have given in the article [Closing](#). And to make the quarters

firm and stiff behind, give some bits of upper leather to slip in between the back piece and quarters, as stiffening, which will prevent the quarters to break at the seat. Tie the whole up together in the vamps, and mark the outside vamp so that you may know for whom they are intended.

In fitting the bottom stuff, be careful that the soles, inner soles, top pieces, &c. are not wider than the last, and that neither is stouter nor lighter than the upper leather requires, and the customer orders: For, by being particular in these things you will be of benefit to your employer and please the customer.

When the shoes are brought from the maker, you are then to see that the seat of the inner sole and fore part is smooth, and then round the quarters even, before they are sent to be bound; do not let the ends of the straps quite meet, but let them be about a quarter of an inch apart, for there will be a better purchase to tie the shoe firm on the foot.

If the shoes be right and left, let the strap of the inside quarter be a trifle longer than the outside, because the inside ankle of the foot is fuller than the outside ankle; therefore it will force the inside quarter more out when the shoe is on, and will bring the ends of the straps to meet even, otherwise the inside quarter will appear shorter, if rounded even.

After the shoes are bound, punch holes in the straps (if to tie) about a quarter of an inch from the end of the strap; and lay the binding smooth by hammering of it gently down on the cutting-board. If the binding be leather, colour the outside of it; and if the upper leather be waxed grain, and it should be any wise rough, put a little soft. paste on it, and with a damp sponge lay the grain smooth; but mind that the paste be well rubbed in, that none of it may appear in any degree on the upper leather.

When the upper leather is got pretty dry, let it then be sized*, and after it is got nearly dry from the sizing, put in the seat piece and label and size it over again; then it will be brought nearly to the same state as when the skins came from the currier.

*Size is made by putting about a handful of white sheepskin shreds to about a pint of water, and let them simmer near the fire for about eight or twelve hours, then strain it to cool.

But if the waxed grain be very close and fine, or if it be dyed on the grain of the skin, sizing only will be sufficient.

So much for shoes; and I think, independent of practice, I have omitted nothing that is needful.

The Method of cutting a Man's Boot.

It is rather singular that the generality of cutters are in. the constant habit of cutting boots at random, that is without a regular and certain rule; though without some rules they seldom attempt to cut shoes; but as boots are of more consequence in the trade than shoes, they ought to have certain and fixed laws.

In the course of my practice I have seen boots from a great many parts of these kingdoms, and from many parts of the continent of Europe; but no two pair of them alike.


The leading shops in the metropolis are not regular in their mode of cutting boots; for from one and the same shop you will see various modes of cutting; which is a convincing proof that there is no regular system or order.

Here I speak from what I have seen; I do not pretend to say that none have taken into consideration the real form and movements of the foot and leg, and have applied a corresponding mode of cutting to answer the end; but, as I have said above, I have seen none.

In the first place it will be proper to show the method, how to take the measure of the foot and leg. We will suppose for a jockey or top boot.

Take the length of the foot as in fig. 5, from C to I, with the size-stick, same as directed in the shoe; then with a graduated piece of parchment* take the width round the foot at E, at F and H; then the width of the heel at c c, then the pitch or the first rise of the calf at D, and the width round the leig at D, likewise the

height of the middle of the calf at B and its width, then the length *a a* and the width round the leg at *a*. If Hessian or Austrian half boots, you must take the length to B, or a little above and width at that height.

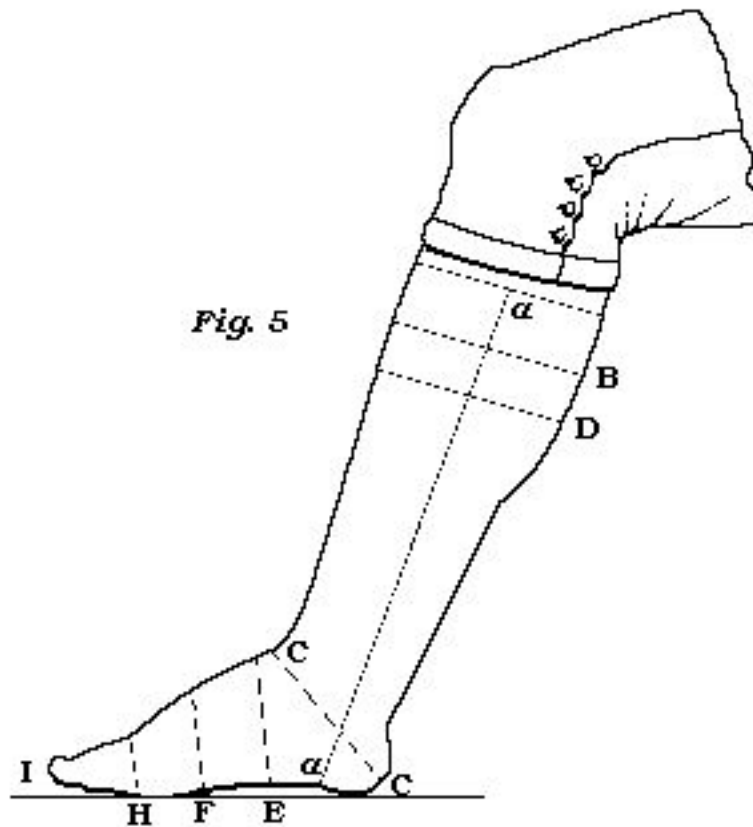


*By making use of a graduated strip of parchment you can enter the dimensions on the order-book; and if there should be no alteration in the person's foot and leg, it will answer at any future period when an order is given without seeing the person. But a slip of paper is liable to many unforeseen accidents.


For the length of a half boot should be up full to the middle of the calf, or above if the leg be small, otherwise it will be very liable to sit loose and open from the leg; because the leg of the boot must be in every part as wide as the heel, otherwise it will be but with great difficulty got on; and there are but few men out of the number that you may measure whose legs below the middle of the calf are fuller than the heel: hence the reason of the above caution.

In the present mode of wearing boots, there is no necessity to take the first rise of the calf, but when the close boot was worn it was found necessary. For I have known a gentleman the first rise of the calf of whose leg was within three or four inches of the ankle, and fuller than his heel; and as close fitting boots were then the wear, and cordovan boot legs, which were taken in very much, and were made as elastic as possible; therefore without attention paid to the first swell of the calf, in cutting his boots, he would always feel too much pressure on the lower part of the calf. Here I caution the young beginner in case close-fitting boots should come in wear.

Now choose out a last that will answer to the dimensions of the foot. A block last is preferable for a boot, because you can form it to the size of the foot and the width of the heel, without being subject to the men, for their care to keep the instab leather in their proper place.

In the next place take the boot vamp patterns, and fit one to the last, and then cut out the vamps from a skin of the substance the work requires, and in the same order as directed for shoes: fold and crease the vamps with the black side out, and cut out the opening as in fig. 6, from *h* to *c*, of the same dimension as that in fig. 7. from *h* to *c*. and something deeper than from *h*. to *K*; and longer than from *e* to *i*, of fig. 7. that you may have room to cut the vamp smooth and even after it is cramped.

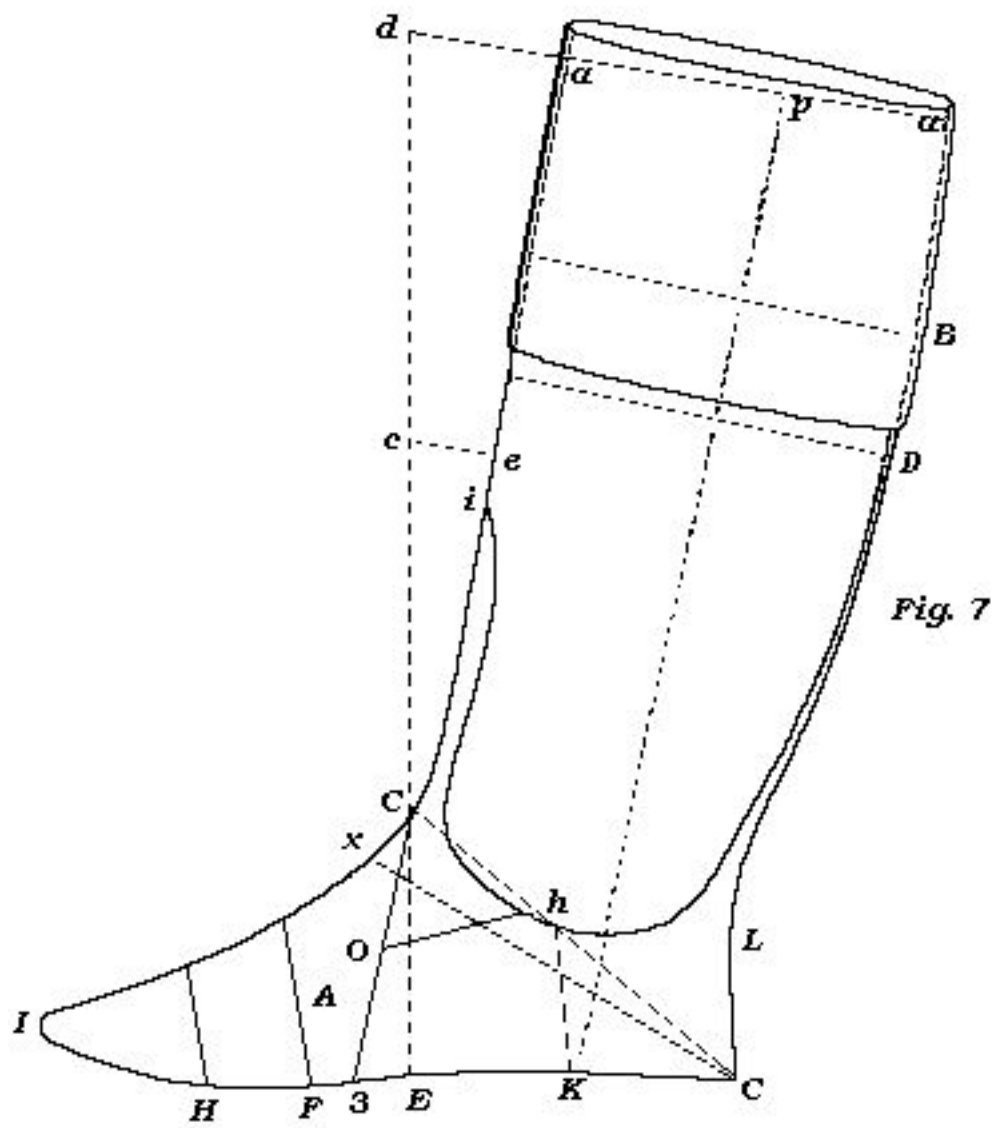

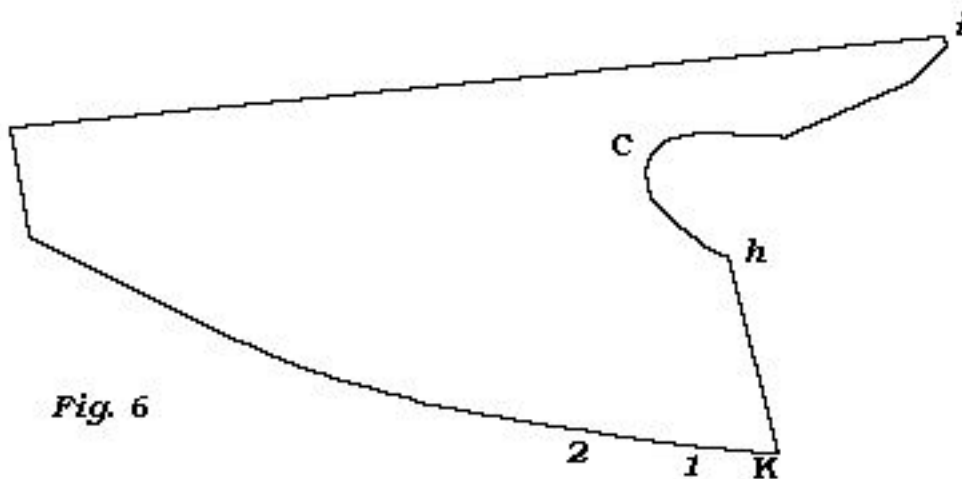

Then wet the vamps, that is, that part that is to be cramped, and with a leather strap, as that of a thin piece of welt, and fix one end of it by a tack at the right end of your cutting-board, and slip the other end of it between the folded vamp, and let it come to lie close against the back of the vamp, with the back part of the vamp towards you, and the end of the tongue towards your left hand. Then at a certain distance from you on the cutting-board fasten the vamp to the cutting-board as at 1 and 2, and then with the left hand strain the tongue of the vamp toward you by the leather strap, and at the same time hammer the opening of the vamp and tongue moderately, with the broad end of the hammer, that the cramp may be retained. After you have cramped both tongues, and laid them smooth with the hammer, take the boot legs and strain out the draft well at the lower part, that there may be as little loose leather as possible about the ankles; and fold them in the middle with the black side outwards.

Though you have these things prepared, I would have you, previous to the cutting of them, to cut the form of the boot in pattern paper.

In fig. 7. is the form of the boot cut to the above dimensions. The side of the vamp *a*, to be exactly the width of one half the vamp, and the end *h K* to be under the ankle, and the lower part at *K* to be within the heel, as the boot will be firmer than when the seam is without, for it keeps the closing seam firm from plying or working.

The depth *h K* to be from two to two inches and a quarter, and to come just under the ankle; and from *h* to *c*, at the instep, to rise in a gradual curve or sweep, so that *c* may be at the bend of the foot at the instep; for if it be above that, the vamp will press too much on the flexor that comes from the leg to the instep to assist in moving the foot, and will cause the wearer to feel the boot rather uneasy. Therefore the width of the tongue of the vamp at that place should not be much wider than from seven-eighths of an inch to that of an inch, that the foot may have a free and an easy movement. Likewise the vamp at that place will sit smoother without wrinkles, much better than when it is very wide. Again, if the quarter of the boot should be lengthened to *x*, the sweep or curve of the tongue of the vamp *h x* will be too much below the ankle and the bend of the instep, and there will be a great deal too much loose leather about the ankles, from the leg and vamp of the boot; and besides having a very awkward and clumsy appearance, it will always sit loose and open from the leg and instep.

Therefore be careful to pay attention to the figure and the above directions, that you may avoid these two extremes, and especially the latter, as it is very awkward and clumsy, and too generally found in boot-cutting.

Let the tongue of the vamp be about three inches and a half from *c* to the point at *i**; and from *c*, to the middle, to run gradually wider till it becomes about an inch and a half wide, and from thence to the end at *l*, to taper gradually to a point.

*That height of the tongue will keep the boot leg smooth in front, and cause it to lie close to the person's leg.

In the next place cut the counter or back strap *b*, and let it join the vamp at *h* K, and to run of a gradual sweep towards the heel, and the depth in the middle between *h* and *L* to be about an eighth of an inch lower than it is at *h**; and the width of the back strap at *L* to be about an inch; and the depth at *L* C to be in general about two inches and a half, which will be nearly at the bend of the heel behind; but from there up the leg let it be about three-eighths of an inch.

*For it will give more ease and freedom to the person's heel to go in and come out of the foot of the boot; but, if higher, it will have the contrary effect, both in feel and in sight.

When taking the width of the heel *c*, you must allow a certain space of the leg below *c*, at the heel, for to come under the sewing, and likewise the counter *b*, must be left wider than the leg, about a quarter of an inch, because of the substance of the leg and the middle piece.

Now let the vamp and counter, or back strap meet at *h* K, and put the last on them, and see that they have the same relation to the last as the vamp and quarter of the shoe, as directed under that article; and if not, you are to cut a little off, of both vamp and counter at *h*, or at K, till they do correspond.

Then take a half sheet of the same kind of paper, and let one side of it be quite straight, to represent the front of the boot leg, and place it under the vamp and counter, in the direction 3. *c. i. a.* for the upper part *a.* to be about two or three inches from the perpendicular E. *c. d.* because, when a man stands upright, the upper part of the leg just under the knee, as at *a*, is between two and three inches from a perpendicular, as *a.* is from *d*; that is, from the perpendicular E. *c. d.*

Three very material things arise from not placing the boot leg in the position of the man's leg: First, if the boot leg be near *a*, perpendicular it will set off in front from the man's leg; secondly, it will be in too great folds behind when the person stands erect; and thirdly, the person will have more trouble to get on such a boot.—And likewise if the length of the quarter of the boot *L c*, be cut as above directed, so as that the wide part of the vamp does not press on the flexor of the foot, and the boot leg to be in a perpendicular position, or nearly so; then the tongue of the boot, and the joining part of the boot leg, will set off from the upper part of the instep and the leg in a loose and clumsy form:—Therefore it will be better for the boot to exceed the position of the leg than otherwise; for then it will sit closer to the man's leg in front, and without any folds behind when the boot is drawn up. and will go on with more ease.

Now you have the leg pattern in its proper position, 3. *c. a.* cut it even with the vamp and counter at the bottom from 3 to *c*, and let the curve of the tongue at *c* meet the edge of the leg pattern, and let the upper point of the tongue meet the edge of the same at *i*, and mark the leg pattern from the point *i* along the curve of the tongue to *h*; and prick two holes with the point of the awl, through the leg pattern, one at *h*, and the other at K.

Then cut off from the leg pattern the marked part till within a quarter of an inch to *h*, then cut it off sloping to *o*.—But mind, when you are cutting the boot leg, that you must not cut off as much from the boot leg between *c* and *i* as the full width of the tongue; because of the draft of the boot leg (commonly called); that is, it must be in proportion to the quantity taken in by the currier to make the leg elastic; which you may see by the given width, on the boot leg, and the apparent one, which you can measure. Then, for an exact measurement, it will be, As the given width is to the apparent one, so will the width of the tongue, to the real width to be cut off from the leg at the tongue.

But in practice you will soon be able to guess the quantity; for it must be a little less than the real width of the tongue, for the above reasons:—Otherwise, if you cut off the boot leg the full width of the tongue or more, you will have the boot leg above the tongue to project out and hang over the tongue, and will remain so, as an incurable subject.

But at *c* the tongue only meets the leg, as in the patterns; therefore at that part there is nothing to be cut off the leg.

Now, after you have cut the front of the leg pattern out, put the vamp pattern to it, and see that they fit ; and if they do, put the weight on both between *K* and *o*; then with the graduated parchment boot measure* take the width of the heel from *c* to *C*; but not, so close to the edge at *c*, without leaving enough to come under the sewing stitch.

* Or, instead of taking the trouble to fold the parchment every time you take the dimensions, you may have a rule made of half the length, just the same as the parchment folded, which you will find more convenient.

Now take the vamp pattern away, and move the leg pattern with its front towards you in length of the cutting-board, that you may have it with more ease within your reach.—(So much for Patterns for exercise.)

Then take the lengths *C D*, *C B* the rise and middle of the calf, and the length *K p*; and the width at their respective lengths. With respect to the small, that is, the space between *L* and *D*, you must be governed by the heel, and the fancy of the wearer :—If the wearer should order them full at the small, the heel will be out of the question; but if he should order them to be rather close, you must be guided by the heel*.—The leg in the small must be left the width of the heel, for the reasons in the last note; otherwise the boot will not go on or come off with ease.—And likewise, it is evident from the same note, that it is not the real width of the heel as *c c*, that makes its way in the boot, but the width of *c e*; and in consequence of the oblique direction of the foot entering the boot, that the boot leg is not required wider than the heel: And practice has taught the trade to know it; though I believe that few observe the cause.

*Here, I would have the young tyro observe, that when a man puts on a boot, when the foot is about half way down the leg of the boot, the rising part of the foot, the middle between the upper part of the instep and the great toe (or what the anatomists call metatarsus) is a collection of bones, five to number, and in many feet it protrudes very much.— This part presses against the front of the boot, and the tip of the heel against the hind part, and the line of their position is in an oblique direction, as the line *h iin fi.8*.

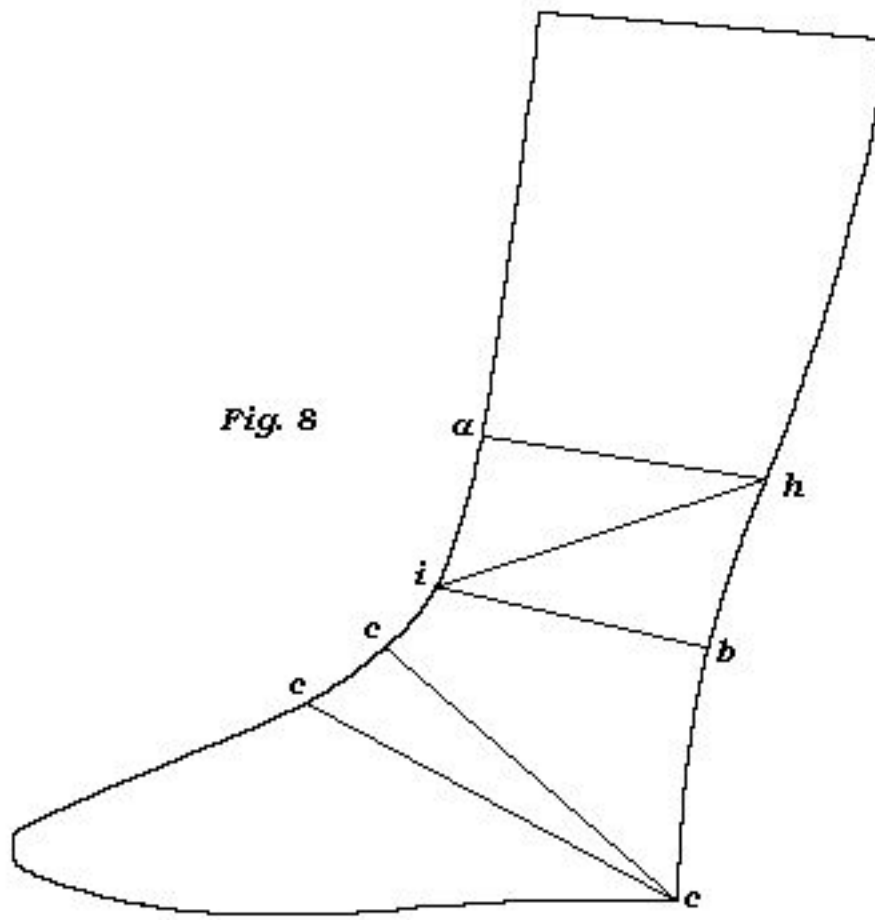


Fig. 8

And this part of the foot is nearly three inches lower down in the boot, as at *i*, than the tip of the heel at *h*.—Now *a h*, and *i b* are parallel to each other, and the angles at *a*, and *b*, are nearly right angles; and take them as such, we have an easy rule to find the width *i b*, or *a h*, by squaring *i h*, and taking the square of *i a*, or *b h*, from it, and the square root of the difference will be the width at *a h* or *i b*, and it will be found a trifle more than the width of the heel *c c*. But when the heel goes down to *b*, the rising part of the foot will be down in the foot of the boot at *c*; therefore at *b*, the boot leg may be cut something less than the heel, as the foot is getting far into the foot of the boot.—As the leg will admit to be cut under the width of the heel at *b*, you can cut the boot sloping from *c* to *b* to fit the form of the heel, which will cause that part of the boot leg to sit closer round the ankle than if the leg was left wider at *b*. Though lately, fashion has prevailed over the natural form of the heel of the boot, by cutting the boot from the lower part of the heel to the calf in a curve projecting from the heel; so that the wearer is not able to keep his foot firm in the foot of the boot; because the form of the boot gives room for his heel to slip up and down in the heel of the boot.—So much for fashion.

Though the heel be the guide for the boot leg in the small, I have known persons to get on boot near two inches less than the heel; but they were persons who had no protruding part on the instep, and who could straighten the foot at the ankle very much.

And I have known others who could hardly move the ankle joint from that of a walking posture without any apparent cause: therefore a certain allowance was necessary above the width of the heel.

By observing the foot coming out of a boot, you will see that after the person's foot comes just out of the foot of the boot, the tip of the heel will press against the back part of the boot leg, and force it into a curve, till the heel comes to the full of the calf; then the heel in general is lost in the width.

The front of the boot leg is straight, and the room for the heel must be behind; but it should not be much fuller than the width of the heel, only that it should go on and come off with ease.

Some would wish to have always their back strap boots, whether Austrian or jockey, to keep that curve that the heel makes, like that of a Hessian boot; but to effect that, they should often be put on the boot trees, and previously damped; then left on till they become perfectly dry.

Now, after these observations concerning the heel and the small of the boot leg, let the boot leg be cut behind as per fig. 7. in the direction C, L, D, B, *a*, to the real width of the person's leg, and especially at B and *a*; but at D it may be left to the fancy of the times or the wearer; but if ordered to fit the leg at that part, you must cut it to the measure.

Almost all boot legs have the width at the small marked on them; and if not, you may cut a narrow strip off the bottom of the boot leg, and strain it out well, and it will give the width by measurement.—The real width of the boot leg at the small, and the narrow part of the tongue of the vamp between *c* and *i* are to be added together, and the sum to be compared with the width of the person's heel; and after allowing a certain portion more than the real width of the heel, that is, for what may be taken in by the closing, cut off the difference from the boot leg, as from L to D; if the boot leg be wider than the heel, &c.

Now you have cut the leg to the size, mark off the length as at *a*, *a*, fig. 7. quite square; and if it be a whole boot leg, (though very few of them are used now, on the account of the tops) mark off the length of the top from *a* *a*, to the length it is to be, and cut the remainder off; but let the bind part of the lower part of the top be about a quarter of an inch deeper than the front, because the projection of the calf requires it, to appear even in prospect.

Then fold the leg at *a*, and let the top part come between the boot leg and the cutting-board, and let them be even in front; then cut the top part to the leg, but not quite close at the lower part of the top.

But if the top is to be sewed on, let the boot leg be about a quarter to half an inch shorter than the real length is to be, and cut a paper pattern for the top.

First fold half a sheet of any kind of paper, and put it under the boot leg on the cutting-board, and let the folded part be even with the front of the boot leg, and cut it even with the upper part of the boot leg, as at *a* *a*, fig. 7. that you may have both ends to correspond; then fold as much of the top pattern at the same end, as the boot leg is too short, and from that fold mark off the length the top is to be, and cut the remainder off. But as I mentioned above, for the whole boot leg let the lower part of the top pattern behind be deeper than the front, about a quarter of an inch; but if the leg be full, half an inch will not be too much.

Then put the boot leg on the top patterns, and let the upper part of the boot leg meet the folded part of the pattern, and be sure that they are even in front; and then cut the pattern behind to the leg. After you have cut out the tops by the pattern, let there be some fine whity brown paper pasted on the inside of the top, to prevent the oil from the leg getting into the top: For the modern boot tops, dressed as they are in acids and alkali, will imbibe every kind of liquid that may come in contact with them.

The counters or back straps are to be cut as above directed. Then you must fit up the boot legs with side linings, and good middle piece to put between the counter or back strap and the leg, and to be so long as to come beyond the heel on each side; for, as there is no feather to the inner sole of the boot behind, unless there is a proper substance at the counter to prevent the boot leg to bend short at the heel, the boot leg will soon crack and break off at the heel.

Now to close this article I shall make one general observation.

Always be careful to place the boot leg as near as you can in the position of the person's leg, (for the above reasons) as in the direction 3. *c*, *i*, *a*, fig. 7.

The counter, or counter part of the back strap, should be up as high as the bend of the foot at the heel, about two inches and a half, as C L; then from the top of the counter, let there be a gradual sweep or curve from L to *h*, and from *h* to *c*; that is, the sweep to come from the bend of the heel behind gradually under the ankle, and then up to the upper part of the instab, nearly to the bend of the foot at that place; but so that the flexor of the foot may have a free movement.

But mind, it should be no lower down, as in the direction of *h x*; there it will have a very awkward appearance, besides its giving too much loose leather round the ankles.

Let the tongue of the vamp be cut so that it may be rather strained in the length, in the closing, than be too full.

When you have obtained that experience, so as to be able to cut the boot at the ankle to any form, at your own will and pleasure; then the other parts will become perfectly easy: and till you have mastered that, be constantly in the habit of cutting patterns to answer the end, to fit the foot and ankle.

Hessian Boots.

Hessian boots were first brought into this country from Germany in the beginning of this war, about 1794 or 1795. Then they were crinkled in the front of the instab; as the present mode of blocking them was, I suppose, unknown to the Germans.

That which I believe was the effect of necessity: in Germany, became a subject of choice in this country, and improved upon.

The form of the boot at first was rather odious, as the close boot was then in wear; but like many fashions, at first frightful, then pitied, and at last adopted; so with the Hessian boots, and they have now given the fashion to all other kinds of boots made with elastic boot-legs.

Hessian boots are in general closed on the in side, but some are closed on the outside; some with back lining, and some without; but those with back linings are the best, they keep up better, and the counter is prevented from slipping under the heel.

Figs. 9. and 10. represent the front and back of a Hessian boot.—Figs. 11 and 12 represent the blocks, which any part of the country may have from London, Bristol, or from any other city or large town.

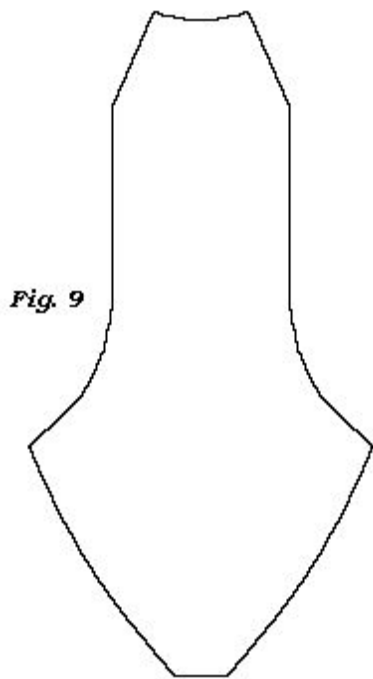


Fig. 9

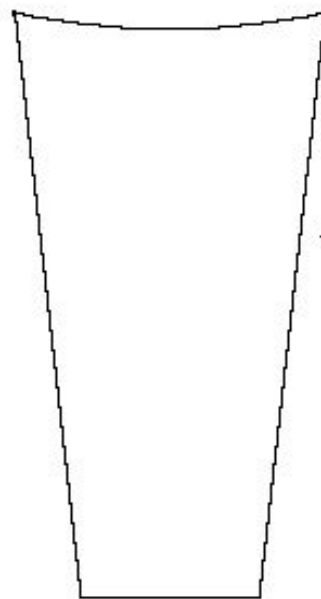


Fig. 10

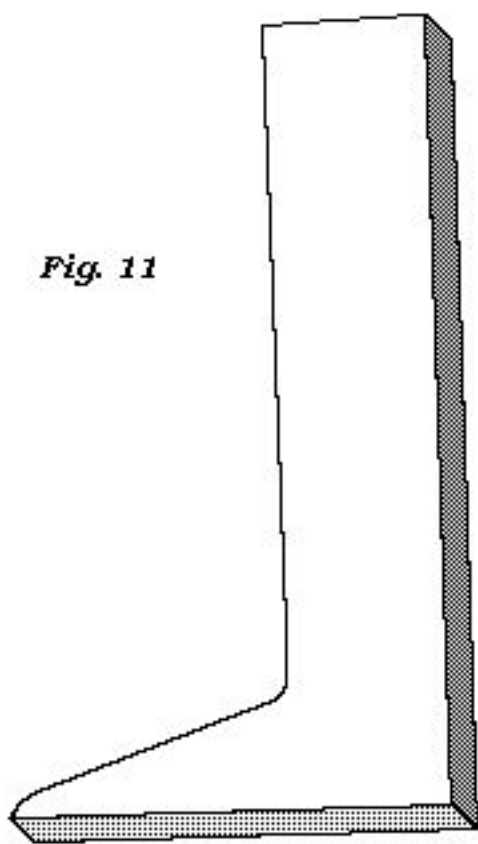


Fig. 11

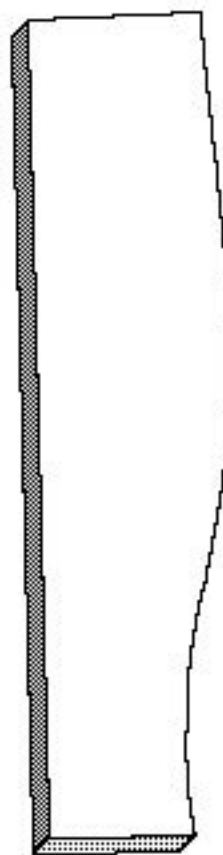


Fig. 12

When blocking the legs, let them be first wetted in cold water; or if the leather should be rather stiff to work, and you think that warm water will render it more pliable, let them be wetted in warm; but mind that the warm be not beyond blood heat; otherwise, if it should be, it will scorch the leather, and render it of very little service.—For the fibres of the leather are very similar to the feathers of a quill: when a certain quantity of heat is applied to them, they will be scorched, and twisted into various directions: so will the fibres of the leather feel the heat alike if above blood heat, though you may not very sensibly discern the process.

Therefore, I would have you to be careful never to use hot water, if you can avoid it by any means.

When laying the front of the boot-leg on the block, mind that the first two tacks are put on each side of the block at the angle *b*; and that the leg be well strained across the instep in the direction *a, b*.—Then strain the leg down the foot, and up the leg to the shin, with tacks on each side, about an inch or two from each other, and work the folds in well at every tack, till you get it quite smooth as if there had been no fold, but one direct piece of leather.

The back lining and counter must be pasted to the back part-of the leg before you block it, and that is to be only strained direct across the block.

When dry, take them off the blocks, and press them flat before you begin to cut them

In cutting them, you must endeavour to let the seam at the lower part of the leg on each side come within the heel of the boot; and, if possible, both the front and back to be cut straight by a ruler from one end to the other; and for the front and back to be nearly of the same width from the lower part of the calf up to the top; but from the calf to the ankle the width of the back must be decreasing to come within the heel at


the bottom; and both, in the small, to be the width of the heel, will be sufficient; but if the calf be full, then, the leg from the ankle to the calf must be left gradually fuller than the heel, that the leg may be of a regular sweep.

If the small of a Hessian boot be left fuller than the heel, it appears, I think, very unsightly.

Indeed, many don't like the Hessian boot, because it retains the swell or curve the heel makes in going on; therefore they make choice of the back strap boot, though the heel makes the same swell in going on; but in consequence of the boot leg being elastic, it closes to the small of the leg after the boot is on.

Please to mind, in cutting the sides of the front and back part of the boot leg, from the ankle to the bottom, to bring them to the width of the heel, that they may be quite straight; or if they meet at bottom, and at the ankle, and: not quite so in the intermediate space, the boot will fit the closer about the heel.

With respect to the form of the top of the Hessian or Austrian boot, they depend entirely on the fancy of the time: Lately they were of a gradual sweep in front, and with a peak behind as in fig. 13; but now they are square in front and without a peak behind, as in fig 14.

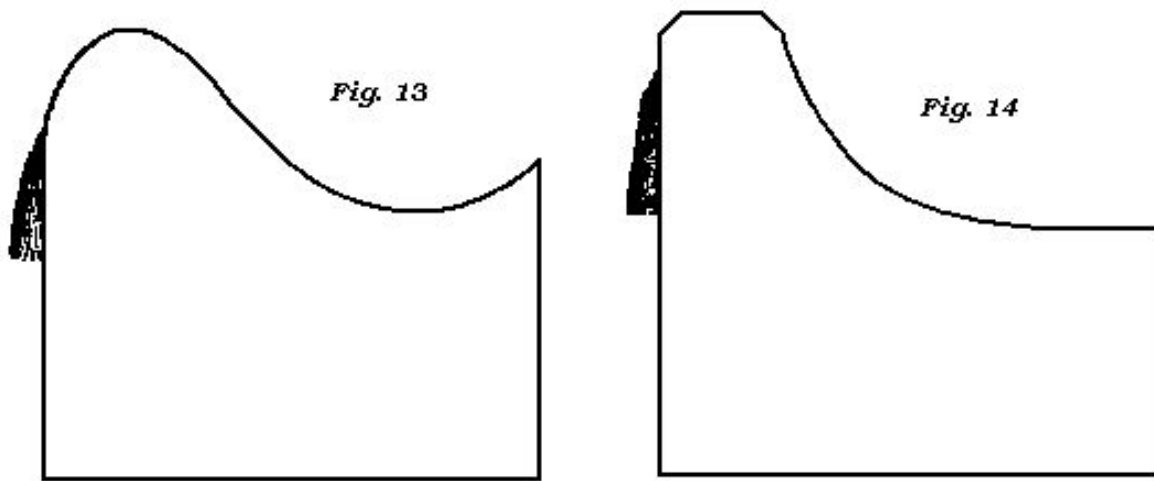

In right and left half boots the opening at the top of the boot leg ought to be cut from a quarter to half an inch on the inside of the leg from the middle: Because the distance from the middle of the calf to the shin, on the outside of a man's leg, is greater than on the inside from the calf to the shin; and as the shin appears to be the middle of the front of the leg, the front of the boot should be made to correspond; otherwise, if the opening be cut in the middle of the boot leg, it will appear, when on the man's leg, too much on the outside of the leg.

But in a straight footed boot you cannot avoid it, nor does it appear so much as in a right and left.

The inside of the top of the front should be lined with yellow roan, or any other kind of leather, morocco, &c.

When treeing the boots, (as the trade calls the putting the boots on the boot-trees,) the boot trees ought to be sorted so, that at the calf they may be the real width of the calf of the leg of the person they are for, if they can be got, or very nearly so: the other parts will in general be in proportion.

After you have got the boot properly on the tree, lay down the seams smooth; and if the boot leg is got rather rough in the working, let there be put on it a little paste, and with a damp sponge let the roughness be laid smooth: when dry, let it be well sized, and, after it is dried of the size, and if you should not find the leg so smooth as you would wish, let it be slicked with the long-stick, and then size it over again; but, previous to the second sizing, some will rub it over with a little candle grease, or mutton suet.

But if you intend to black: the boot with shining blacking, which is much in practice, you must avoid the grease; though the grease is is not observed after the boot is sized; any more than when the boot legs come from the currier; for that is nearly the process they make use of to grain the wax-leather, and the trade endeavour to recover the lost grain by the same means.

The top leather (if a top boot) is only to be washed with fair water and a clean sponge; and if there be any wrinkles caused in the working, they may be laid smooth with any clean smooth thing, such as a long-stick, a piece of glass, the same as the curriers make use of. Let the top be dry before you take the boot of the trees.

Laced Half Boots.

The measure of a laced half is to be taken at the heel and foot, the same as the boot; but above the ankle you must take the real width of the person's leg, as at $b\ b$; and at the length as at $d\ d$, fig. 15. Here the whole space, from $a\ a$ to $d\ d$, is in one piece, the leg and quarter; and the vamp from $a\ a$ to the toe. The position of the half boot is the same as the boot,. in proportion to the length: for example, suppose that e (in fig. 7.) is the length of the half boot then as the whole length $c\ d$ is to the half $c\ e$, so is the distance $a\ d$ from the perpendicular to $e\ e$, the distance at the length of the half boot, and so for any length. But in practice there will be no necessity to come to mathematical proportion; for your daily experience, with attention will fix the form in the mind sufficiently exact for all purposes, without having recourse to the above method.


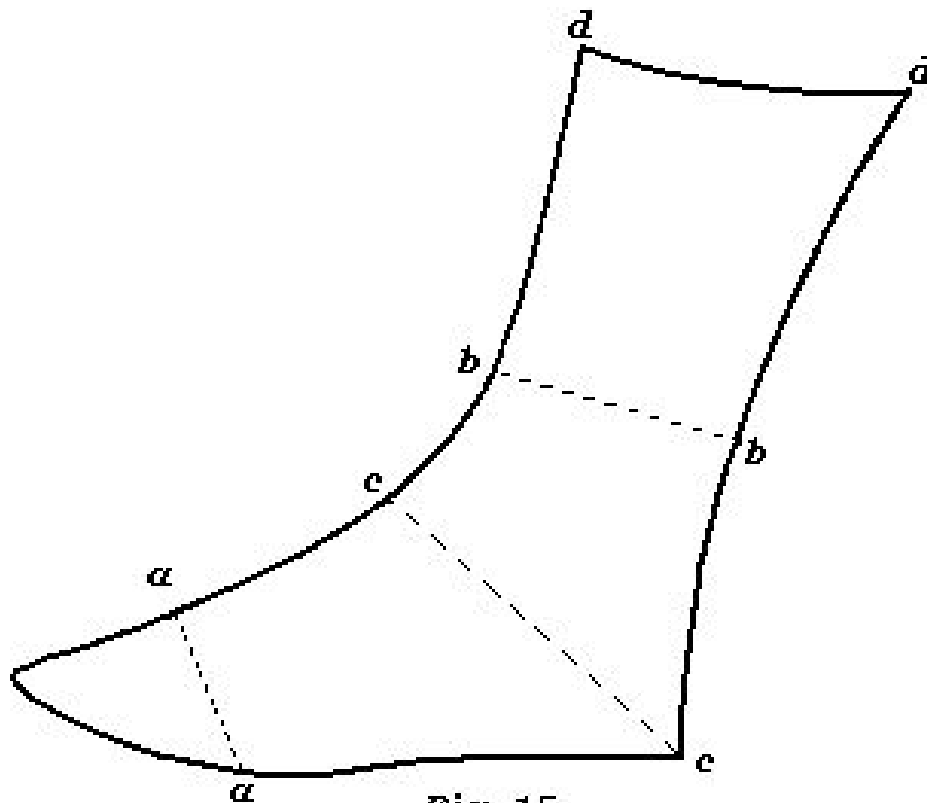


Fig. 15

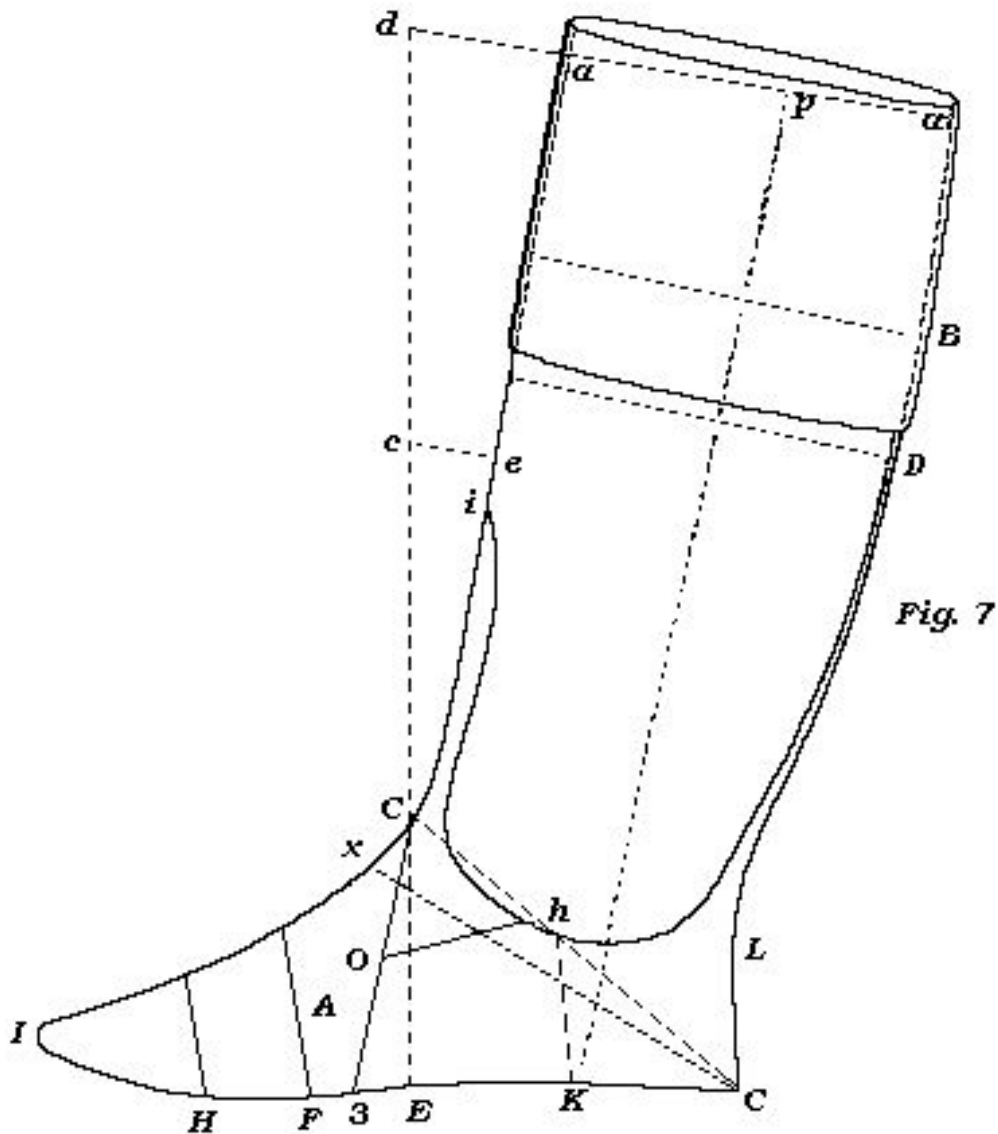

I have only laid that down, that you may have an idea of the principles.

The side *a c b d*, (fig. 15) is open to be laced up in front, with a piece of thin, leather all the way up under the lacing; and both sides are to be lined with a strip of leather about half an inch wide, to strengthen the leg under the lacing.

The leg of the half boot must be cut as near at you can to the real width and form of the person's leg, in front and behind.

Laced half boots are not much worn at present; but the fancy of mankind is so uncertain, that the trade do not know how soon they may come into general wear.

Women's Shoes, or Slippers.

The dimensions of the foot are to be taken the same as directed for the men's.—If there is to be a wood heel of any height, you must choose the last to have a hollow in the waist, and a spring or pitch in proportion to the height of the heel.

In the next place, you must fit the patterns to the last; observing the same directions as given in the men's.—Some like the quarter long, some short, and some middling.—Some like the quarter deep behind, and some rather low; therefore a general rule cannot be observed, but you must be directed by the customers.—A wood

heel should not have the quarter so deep behind as a flat heel.

The quarter of a Morocco, kid, or any wove upper slipper, from two to two and a quarter deep behind is sufficient; but to strong leather shoes, or slippers, the quarter ought to be deeper as the substance of the shoes and the wearer require them.

In general, we find the wearers of Spanish, Morocco, kid, or any kind of wove slippers, wish the length of the front of the vamp of the same length, whether the foot is long or short.

The common wearing length now in use from the open part of the vamp to the toe, is from two to three inches; therefore the length of the whole vamp has no need to be more than from three and a half to four inches long. That is, that part of the vamp which joins the quarter to be from an inch to an inch and half from the open part of the vamp; for, if the joining of the vamp and quarter should be nearer to the front of the vamp than above directed: the join will be more liable to tear.

From the above length of the vamp, the length of the quarter must be in proportion to the length of the foot. The quarter should be something deeper behind than at the side, even to those that desire the quarter straight; for, if the quarter be cut in a straight line from the sweep of the front of the vamp to the end of the heel seam, it would appear in the slipper rather of a rise or swell in the middle than straight; therefore the quarter should be from an eighth to a quarter of an inch lower at the side than behind, and let it be in a gradual sweep from the top of the heel seam to the front of the vamp, as per fig. 16. So much for hollow vamps.

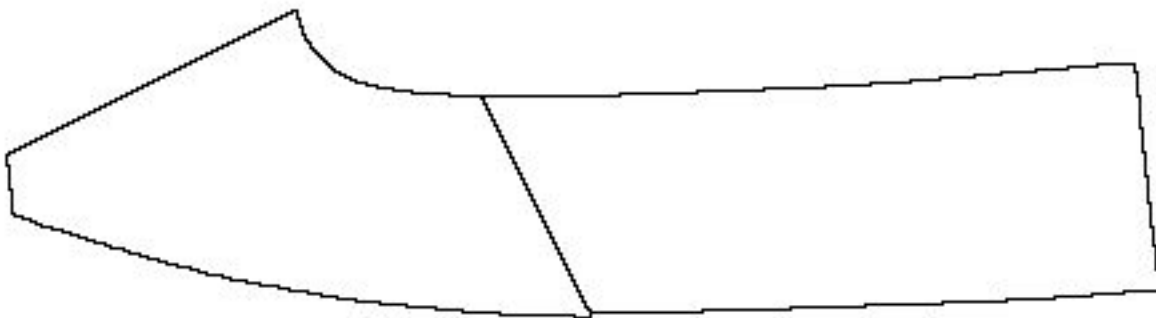


Fig. 16

But in vamps with peaks in front, (to which some old people are still partial, from being the fashion when they were young,) the quarter comes to the angle the peak-makes with the vamp, as in fig. 17.

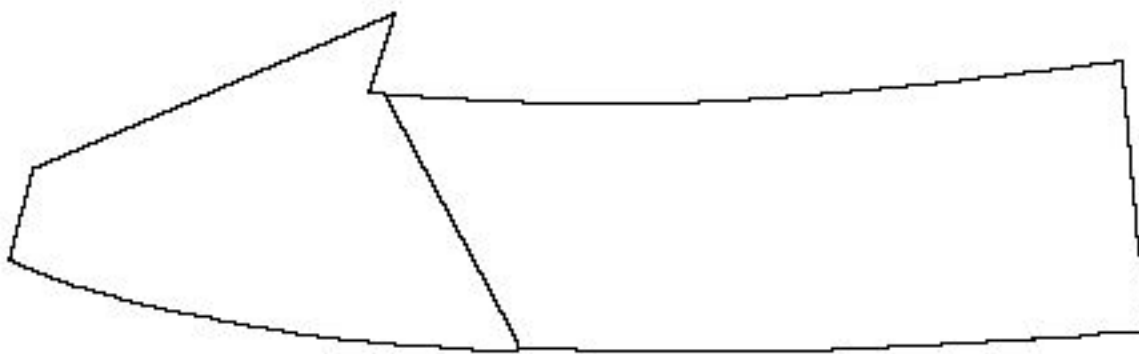


Fig. 17

The Grecian or sandal form should be cut as per fig. 18. A ruler placed along the upper part of the quarter, and within two inches of the toe, will give the line of direction, as *a b* on the vamp, where to cut the scollop from; the end of the quarter must form one of them, as per fig.

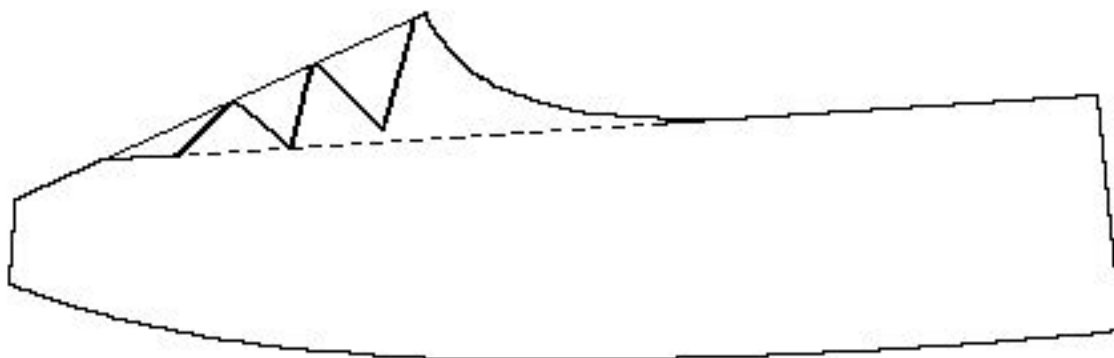


Fig. 18

Whatever form or shape fancy may invent in future, they may be deduced from the above modes: And as to all shoes to tie, they are similar to those of the men's; to which refer.

In all women's work, except coarse leather pumps or shoes, you must be careful to cut them even, smooth, and exact, to what you intend them to be, for when they are bound there is no future remedy.

All Spanish, Morocco, and kid skins are to be cut the same as directed to cut men's upper leathers from the calf skins.

In all wove uppers and linings, the width of the vamp and length of the quarter are to be taken in the length of the piece, whether it be velvet, silk, jean, &c.


The quantity to be turned in by the binder, ought to be pricked off at the heel seam and side seam of the quarter pattern as well as the vamps, if all the lining be cloth, that the binder may not turn in more nor less; otherwise you will not be sure to have the real length of the quarter, or vamp.

Leather lining in the quarters is to be cut close to the patterns; for the binders do not not turn any in, but let them meet at the edges.

In all Spanish, Morocco, or any kind of leather that is to be closed at the sides and heel seam and bound with leather, certain allowance is to given in the vamps and quarters, that you may retain the real length of the quarter and vamp; but if they are to be bound with silk, there will be no need for any allowance, because the binder in this case only lets the edges meet.

Women's Half Boots to lace.

This article varies very little from that of the men's, as in fig. 15, which look to.

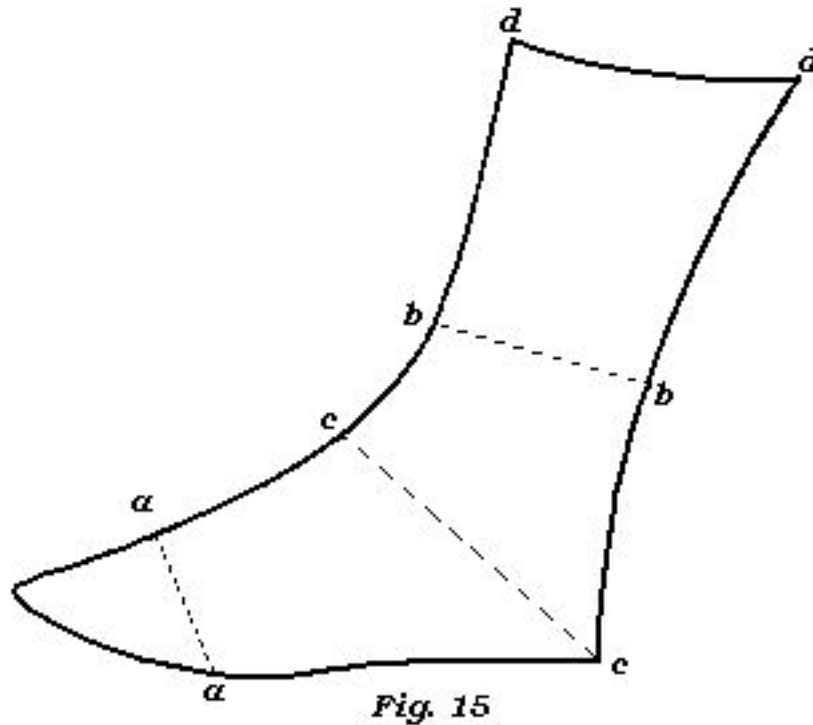

The length of the quarter in the women's is something longer, that is, *a a* is nearer the toe.

If the heel be high, the boot leg must have more pitch, that is, it must be further from a perpendicular, and that in proportion to the height of the heel.—In every other respect you must follow the directions given in the men's, in any kind of leather; and in any kind of wove, with the additional directions in the wove upper slippers.

To cut up Hides for Soles.

In the first place, let the hide lie flat on the floor or board; then round off the loose belly and shanks, and cut off the neck and the thin part of the shoulders across the width of the whole hide.—Then cut the rest of the hide in ranges across the hide, of such width as you may require.—. There is no need for the ranges to be wider than the width of the last at the joint added to the width in the small; for in the prime part of the range the soles may be taken heel and toe; that is, in cutting the soles separate, where the heel of one comes, the toe of the other will come: Hence, there is no need for the range to be so wide as twice the width of the last at the joint.

It has been found by various trials in different modes, that cutting up sole leather in ranges is the simplest, and with the least waste.

The neck part is in general converted into welt leather; the loose belly, and part of the shanks, into inner soles; and the hard shanks into lifts, split-lifts, and piece soles.